

https://dspace.org/

Stress concentrations around an axisymmetrically attached nozzle on a glass reinforced plastic hemispherical dome

Combley, James Harold

2015-01-14
http://hdl.handle.net/10539/16527

Downloaded from a DSpace repository. https://dspace.org/

STRESS CONCENTRATIONS AROUND AN AXISYMMETRICALLY ATTACHED NOZZLE ON A GLASS REINFORCED PLASTIC HEMISPHERICAL DOME.


James Harold Combley.

A dissertation submitted to the Faculty of Engineering, University of the Witwatersrand, Johannesburg, in the fulfilment of the requirements for the degree of the Master of Science in Engineering.

Johannesburg, 1987.

DECLARATION

I declare that this dissertation is my own, unaided work. It is being submitted for the Degree of Master of Science in the University of the Witwatersrand, Johannesburg. It has not been submitted before for any degree or examination in any other University.

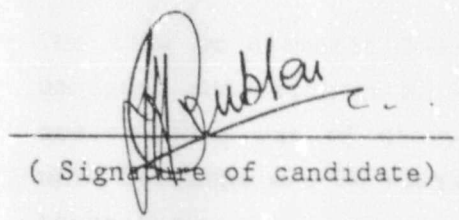

(Signature of candidate)

4 day of DECEMBER 1987.

ABSTRACT

The need for intensive research on an aspect of hand-laid-up vessels was considered relevent for validating the theory provided in a locally used vessel design Standard. This resulted in the stress concentration around an axisymmetrically placed nozzle on a hemispherical dome being analysed.

The 1054 mm diameter dome and the 100 mm diameter nozzle attachment were designed according to BS 4994 (1985) for a test pressure of 2 bars. The construction was of chopped strand mat and woven roving cloth laminated with Derakane 470-36 vinyl ester resin using the handlayup manufacturing technique.

The hemisphere was hydraulically tested up to a pressure of 1.6 bars at 0.1 bar intervals. Strain readings were obtained in both the hoop and the meridional directions, inside and outside the vessel wall. The data obtained permitted the determination of the the midplane strains , curvatures, forces, moments and stresses using the principles of Classical Lamination Theory.

An analysis was made of the bending and plane stress components together with a comparison of the experimental results with those obtained using two isotropic computer models.

The findings have provided information regarding the use of symmetrical laminates on the vessel wall and the asymmetrical laminate requirement of the nozzle overlay region. The validity of using simple FEM models to predict the stress distribution around the attachment is shown with proof that the BS 4994 vessel design code provides theory adequate for the design of nozzle overlays on internally pressurised hemispherical domes.

ACKNOWLEDGEMENT.

My thanks go to the following companies and members of the University for the assistance and generous financial support which they provided for the duration of my Masters Degree.

Mr. A. Mitchell :Acoustical Fibreglass Insulation (Pty) Ltd.
Mr. S. Harold :Acoustical Fibreglass Insulation (Pty) Ltd.
- for the donation of glass reinforcements
- for their encouragement and financial assistance

Mr. R. Scheepers : Dow Chemicals (Pty) Ltd
- for the donation of resin

Mr. A. Carter : Fibrewound (Pty) Ltd.
Mr. P. Kirkwood : Fibrewound (Pty) Ltd.
- for advice and the construction of the hemisphere

Drs. R. J. Fritz : School of Mechanical Engineering
- for his guidance and advice

Members of the Mechanical Engineering Workshop
- for their assistance in setting up the testing rig

Ms. J. S. Attwood : Computer Centre
- for her assistance in software development
- for her continual support in editting the thesis
Ms. J. M. Botha : Computer Centre
- for her unfailing patience in typing my thesis

I wish to also extend my sincere thanks to the members of the Reinforced Plastics/Composites Facility and particularly to my Supervisor, Mr C. Diamantakos who for the past two years has been a source of unfailing encouragement and assistance in the furthering of my academic career. For this, I am extremely grateful.

DEDICATION

This work is dedicated to my parents, Jim and Magdeleine, for the abundant love and guidance which they have always given me, and to my dear wife, Julie, whose patience and encouraging words strengthened me during the difficult stages of the project.

To my late brother, David. The fond memories of the times we shared together remain. May Love never seperate us.

TABLE OF CONTENTS

1.0 INTRODUCTION 1
1.1 Literature Survey 3
1.1.1 Pressure Vessel Design Procedures 3
1.1.2 Stress Concentrations Around Nozzle Attachments . 8
1.2 Purpose and Aims 13

2.0 PREPARATION AND TEST PROCEDURE 15
2.1 Design of the Hemisphere/Nozzle testing rig 15
2.2 Determination of the Mechanical Properties of the Materials used 18
2.2.1 Pre-Test Specimen Analysis 18
2.2.2 Post-Test Hemisphere Wall Analysis 19
2.3 Preparation of the Test Rig and Equipment 21
2.4 Test Procedure 28
2.5 Processing of Data 31
2.5.1 Correction of the Experimental Strains 31
2.5.2 Lamination Theory 33
2.5.3 Element Laminate Structure 34
2.6 Brief Description of the Computer Models 35

3.0 RESULTS AND OBSERVATIONS 44
3.1 Dimensional and Property Characteristics of the Strain Gauge Laminate Elements 45
3.2 Midplane Curvature Distribution 52
3.2.1 Midplane Strain Distribution 54
3.3 Distribution of Unit Forces 57
3.4 Distribution of Unit Moments 59
3.5 Stress Distribution Around the Nozzle 62
3.5.1 Hoop Direction 62
3.5.2 Meridional Direction 65
3.6 Contribution of Stress Components (Bending and Plane) 68
3.6.1 Hoop Direction 68
3.6.2 Meridional Direction 71

3.7 Isotropic Model Comparisons 74
3.7.1 Hoop Direction 74
3.7.2 Meridional Direction 76

4.0 DISCUSSION 77

APPENDIX A. DESIGN OF THE HEMISPHERE/NOZZLE TEST RIG 91
A.1.1.1 Operating and design conditions 95
A.1.1.2 Materials 95
A.1.1.3 Resin 95
A.1.1.4 Hemisphere/Nozzle dimensions 96
A.1.1.5 Material Properties 96
A.1.1.6 Wall Structure of the Hemisphere 97
A.1.1.7 Determination of Wall Laminate 98
A.1.1.8 Nozzle Compensation 99
A.1.1.9 Overlay Laminate Construction 101

APPENDIX B. MATERIAL PROPERTIES 103
B.1 Post test laminate analysis 109
B.2 Normalization of the results 111

APPENDIX C. LAMINATE STIFFNESS MATRICES AND STRESS FACTORS 114
C.1 Laminate stiffness Matrices 114
C.2 BS 4994 Stress Concentrations 115
C.3 Stress Calculations Using BS 4994 115
C.4 BS 4994 : (1987) : Hemisphere Unit Loads 116
C.5 Stress Reducing Factors (SRF) 117

APPENDIX D. TABULATIONS OF THE TEST RESULTS 118
D.1 The Tabulated Experimental Results 119
D.2 The Corrected Strain Values 120
D.3 The Tabulation of the Processed Data 121
D.4 The A, B and D Matrices of Arm B 122

APPENDIX E. PRINTOUTS OF THE COMPUTER MODEL OUTPUTS AND PROGRAMS 127
E.1 Basic Isotropic Model 128
E.2 Basic Isotropic FEM Model 128
E.3 Lamination Theory Program - BIGFOOT 129
E.4 Graphics Computer Program - BIGPLOT 129
E.5 Output from the Truncated Hemisphere Model (1.6 bars Pressure) 130
E.6 Output from the FEM Hemisphere Model (1.6 bars Pressure) 133
E.7 Basic : Truncated Hemisphere Computer Model 138
E.8 Basic : FEM Hemisphere Computer Model 143
E.9 Pascal : Lamination Theory Program 144
E.10 Pascal : Graphics Curve Plotting Program 146

APPENDIX F. ARTICLE 4 - 3 ANALYSIS OF SPHERICAL SHELLS 150

APPENDIX G. FLOW DIAGRAMS OF THE COMPUTER MODELS 154

APPENDIX H. DRAWINGS OF THE TESTING RIG 159

APPENDIX I. REFERENCE 160

LIST OF ILLUSTRATIONS

LIST OF FIGURES

Figure 1. Nominal dimensions of the test rig 16
Figure 2. Dimensions of elements of the nozzle region ... 17
Figure 3. Details of strain gauge arms 26
Figure 4. Elements of the first principles computer model. 37
Figure 5. Element dimensions for the first principles computer model 38
Figure 6. Principle element and relevant variables for the FEM computer model 40
Figure 7. Elements and displacement directions for the FEM computer model 41
Figure 8. Layout of the strain gauge arms 46
Figure 9. Distribution of the woven roving in the compensation region 48
Figure 10. 4-Gauge bridge with one active gauge 104
Figure 11. Flow chart of the first principles computer model 155
Figure 12. Flow chart of the FEM computer model 157

LIST OF GRAPHS

Graph 1. Distribution of Hoop Curvature 51
Graph 2. Distribution of Meridional Curvature 51
Graph 3. Distribution of the Midplane Hoop Strain 53
Graph 4. Distribution of the Midplane Meridional Strain . 53
Graph 5. Distribution of the Hoop Unit Forces 56
Graph 6. Distribution of the Meridional Unit Forces 56
Graph 7. Distribution of the Hoop Unit Moments 58
Graph 8. Distribution of the Meridional Unit Moments 58
Graph 9. Distribution of the Hoop Stress (inside) 61
Graph 10. Distribution of the Hoop Stress (outside) 61
Graph 11. Distribution of the Meridional Stresses (inside). 64
Graph 12. Distribution of the Meridional Stresses (outside) 64
Graph 13. Trends of the Hoop Stress Components (inside) .. 67
Graph 14. Trends of the Hoop Stress Components (outside) . 67
Graph 15. Trends of the Meridional Stress Components (inside) 70
Graph 16. Trends of the Meridional Stress Components (outside) 70
Graph 17. Isotropic Models Stress Comparison (Inside Hoop). 73
Graph 18. Isotropic Models Stress Comparison (Outside Hoop) 73
Graph 19. Isotropic Models Stress Comparison (Inside Merid) 75
Graph 20. Isotropic Models Stress Comparison (Outside Merid) 75

LIST OF PLATES

Plate 1. Components of the test rig 23

Plate 2. Strain gauges attached inside the vessel 24

Plate 3. Strain gauges attached outside the vessel 24

Plate 4. Detail of nozzel backing flange 25

LIST OF TABLES

Table 1. Material properties of the Resin/Glass Reinforcements System 19

Table 2. Normalised Material Properties 20

Table 3. Contents of each laminate element 50

Table 4. Tensile data for specimen type 1. 105

Table 5. Tensile data for specimen type 2. 106

Table 6. Tensile data for specimen type 3. 107

Table 7. Burnoff of the test specimens 108

Table 8. Post test results of the burnoff of element sections 110

1.0 INTRODUCTION

South African industry over the past decade has experienced substantial growth in the use of Glass Reinforced Plastics (GRP) in the chemical process industry. To a large extent this can be attributed to the chemical resistant properties of the resin systems used and the versatility of the material, which permits a vast range of applications in this sector of industry. The question which remains however is, " What is the design basis for the introduction of GRP to the chemical industry, particularly in the vessel and tank market ? "

Considerable progress has been made in the development of mathematical models for analysing the fibre/matrix systems in aerospace technology. These theories may involve invariant stiffness matrix theory or the theories enclosed in classical lamination theory for examining the behaviour of orthotropic and anisotropic materials under load. The theories form a sound foundation for the designer of GRP products but their complexity provides little grounds for use in the general industry.

It was with this in mind that various countries in the late 1960's and early 70's formulated GRP pressure vessel design standards. The most widely known being the German Merkblatt (1969), the American ASME X (1973) and ASTM D3299 (1975) and the British BS 4994 (1973). It became possible for more consistency to be maintained in designing with GRP for a particular application.

To a large extent, the standards are applicable mainly to their country of origin. i.e. ASME X deals with the vacumm bag and filament winding processes whereas BS4994 is primarily orientated towards the handlay up process. Local industry is thus in the position where the necessity arises to gravitate toward

a standard which is geared to the capabilities of its manufacturers.

A survey of internationally recognised design standards reveals that BS4994 is the most suitable standard for use in the South African GRP industry. This primarily results from the extensive design method described which is orientated around the handlayup process and the use of raw materials such as resin and glass mats which are locally available.

The standard whilst being comprehensive in the procedures stipulated has largely been adapted from theory on steel vessels. The necessity for continued research must thus be undertaken to validate the applicability of the models stipulated for designing wall structures, seams and the nozzle compensation laminates in GRP.

Stress concentration is a prime concern in designing vessels built for high pressure applications. Areas such as support atttachments, seams and nozzle attachment areas are some of the more obvious high stress concentration areas found on a vessel. Although general views are to increase wall thicknesses to reduce local stresses, the obvious may have the opposite affect.

It was with this that the author embarked on a project in which the stress concentrations around an axisymmetrically positioned nozzle on an internally pressurised GRP hemispherical dome were analysed. The aim was to validate the theory used in BS 4994 (1985) and to compare the results with those found from simple isotropic FEM models.

It is hoped that a meaningful contribution has been made to furthering our understanding of the behaviour of glass reinforced plastic materials with applications in the industrial sector.

1.1 LITERATURE SURVEY

The survey provides an overview of international vessel and tank design procedures applicable to glass reinforced plastic (GRP) materials. This is followed by literature which pertains more directly to the stress concentrations found around nozzle attachments on pressure vessels and tanks. The difficulty in obtaining literature which deals specifically with this aspect of GRP vessel design has led to the use of information on research undertaken on steel vessels.

The details on stress concentrations on steel vessels has been compared to the relevant GRP vessel analyses where applicable.

1.1.1 PRESSURE VESSEL DESIGN PROCEDURES.

The anisotropic nature of GRP has caused the development of various theoretical approaches for its analysis. These particularly in GRP vessel design, have varied from the isotropic thin shell theory approach to macromechanical theories. The study of GRP laminates in chemical environments however, has further necessitated the addition of safety factor considerations for pressure vessel design. These account for the material strength losses due to chemical stress corrosion and material defects.

Safety Factors:

BS 4994, has approached the design safety factor aspect as follows. It considers vessel lining, manufacturing technique, temperature, cyclic loading and cure applicable. A factor of 3 is included to account for material strength losses due to long term loading. The German Merkblatt (1969) however, suggests a

safety factor together with a material factor. The effect of cyclic loading, inhomogeneities and temperature are contained in the material factor together with an additional anisotropy contribution. The American ASME X (1971), using data accumulated over 15 years, suggests that a laminate stressed at 25% to its tensile strength will have a fatigue life of 250 000 cycles. It also includes that the maximum design temperature is limited to 65 Celsius. BS 4994 however, permits temperatures up to 120 Celsius with a respective temperature factor consideration which is dependent on the heat distortion temperature of the resin.

Anisotropy is not dealt with in BS 4994 and Owen.M.J. (1982) considers this a shortcoming of the Standard. However, as conservative material Unit Strengths and Extensibilities are advised, the transverse and longitudinal material strengths are similar when using balanced woven rovings as glass reinforcement. Owen states that the Standard is solely applicable to the use of balanced woven roving mats and chopped strand mats as vessel reinforcement materials.

The standard further remains unique in that it utilises a unit loading method for determining the laminate thicknesses required. This is as a result of theory derived from BS 2782 (1982). ASME X provides minimum design tensile strength values which correspond to the particular type of vessel manufacture to be used ie. Bag moulding, Centrifugal Casting and Filament Winding. The ASTM D3299 similarly provides a minimum design tensile strength for contact moulding. These are related, in Table 1 of the Standard, to the expected thickness of the laminate. These figures also show an increase in the tensile value with thickness. Whilst these expected strengths may be valid in the short term, none of the standards provide safety criteria for vessels in aggressive chemical enviroments over long term periods. This would largely be dependent on the type of liner used and its material and method of construction.

Author Combley James Harold
Name of thesis Stress Concentrations Around An Axisymmetrically Attached Nozzle On A Glass Reinforced Plastic Hemispherical Dome. 1987

PUBLISHER:
University of the Witwatersrand, Johannesburg
©2013

LEGAL NOTICES:

Copyright Notice: All materials on the University of the Witwatersrand, Johannesburg Library website are protected by South African copyright law and may not be distributed, transmitted, displayed, or otherwise published in any format, without the prior written permission of the copyright owner.

Disclaimer and Terms of Use: Provided that you maintain all copyright and other notices contained therein, you may download material (one machine readable copy and one print copy per page) for your personal and/or educational non-commercial use only.

The University of the Witwatersrand, Johannesburg, is not responsible for any errors or omissions and excludes any and all liability for any errors in or omissions from the information on the Library website.