DSPACE

https://dspace.org/

Modification of the cast structure of stainless steel AISI310s and its influence on mechanical properties

Ozbayraktar, Serdar

1992
https://hdl.handle.net/10539/27915

Downloaded from a DSpace repository. https://dspace.org/

7.4 The Relationship Between Microstructure and Macrostructure

There is no doubt that macrostructure and microstructure are linked and that a change in one will bring about a change in the other. However it is not entirely certain whether the microstructure is determined by the macrostructure or vice versa. Furthermore the relationship between primary arm spacing and grain size is not known. Previous researches suggested either a directly proportional relationship[243], i.e. as one increases the other one also increases and vice versa or no relationship[216] at all. This section is an attempt to clarify the relationship between the microstructure and macrostructure of as-cast metals utilizing the data obtained for the as-cast structure of AISI310S during the course of this work and the model proposed for primary arm spacing in the previous section.

In order to simplify the picture the following points should be stated:

(i) the change in the width of a single macro grain per unit time (that is in the direction perpendicular to the direction of heat flow) is directly proportional to the change in the primary dendrite arm spacing per unit time. This relationship could be expressed as:

$$\frac{\delta gw}{\delta t} = n \frac{\delta \lambda_1}{\delta t} \qquad \text{7.32}$$

where gw is the columnar grain width, λ_1 is the primary arm spacing, and t is the dimensionless time which is zero at the onset of nucleation in the melt and n is the number of primary arms in the grain. In strongly columnar structures as in the present

case and as in almost all continuous cast structures, this relationship could also be expressed as follows:

$$\frac{\delta gw}{\delta X} = n \frac{\delta \lambda_1}{\delta X} \quad \ldots\ldots\ldots\ldots\ldots\ldots\ldots\ldots\ldots\ldots 7.33$$

where X is the distance between the moving solid/liquid interface and the point where a specific grain is nucleated.

Integrating equations **7.32** and **7.33** would give the same result, assuming the integration constants to be zero:

$$gw = n\lambda_1 \quad \ldots\ldots\ldots\ldots\ldots\ldots\ldots\ldots\ldots\ldots 7.34$$

(ii) However, there arises the question of how the number of primary arms in the grain is determined. If the constitution of the alloy and other casting parameters such as mould size and shape, ambient temperature, amount poured and time of pouring, are kept constant, superheat becomes the only influencing variable. In the present work pouring was carried out at predetermined degrees of superheat and the primary arm spacing might be expected to be directly related to superheat.

Based on the grain width and dendritic arm spacing measurements carried out on ingots cast from different temperatures, and the regression analyses done using these results, a quasi-empirical model will be proposed to formulate a relationship between the grain width and the primary arm spacing. This relationship is linked to the theory of constitutional supercooling. An attempt will be made to derive a model that will fit the results of experiments carried out with superheat as the only

controlled variable.

When the data for grain width measured at 6 mm and 14 mm distances were analyzed statistically, the equations found were of the form:

$$lngw = a - b\left(\frac{1}{\Delta T}\right) \quad \ldots\ldots 7.35$$

This equation can also be expressed as:

$$gw = e^{\left(a - \frac{b}{\Delta T}\right)} \quad \ldots\ldots 7.36$$

The regression equations gave the relationship between grain width and ΔT for base metal as:

$$lngw_6 = -1.778 - 113.711\left(\frac{1}{\Delta T}\right) \quad \ldots\ldots 7.37$$

and

$$lngw_{14} = -1.784 - 81.513\left(\frac{1}{\Delta T}\right) \quad \ldots\ldots 7.38$$

They could therefore be expressed as:

$$gw_6 = 0.169\, e^{-\frac{113.711}{\Delta T}} \quad \ldots\ldots 7.39$$

and

$$gw_{14} = 0.168\, e^{-\frac{81.513}{\Delta T}} \quad \ldots\ldots 7.40$$

As can be seen, although the point of measurement moved from 6 mm to 14 mm, the coefficient of the right hand side remained almost constant, whereas the numerator of the exponential term dropped by **1.395** times. The significance of these observations will be shown in relation to the results of the analysis of arm spacings since these analyses could explain the difference in the

values of the numerators of the exponential terms in equations **7.39** and **7.40.**

When the base metal data for primary arm spacings measured at 6 mm and 14 mm distances were analyzed statistically, the equations found were of the form:

$$\lambda_1 = a + b \ln \frac{1}{\Delta T} \quad \ldots\ldots 7.41$$

This equation could be expressed in a general form as proposed in the previous section.

Thus,

$$\lambda_1 = \frac{D}{\alpha_1 R^a} \ln \frac{mC_o(1-K_o)\alpha_2 R^b}{DK_o \Delta t} \quad \ldots\ldots 7.42$$

Using the regression equation for λ_1 at 6 mm from the chill zone:

$$\lambda_1 \ (6mm) = 0.04733 + 0.007354 \ln \frac{1}{\Delta T} \quad \ldots\ldots 7.43$$

it can be shown that

$$\frac{D}{\alpha_1 R_6^a} = 0.00735 \quad \ldots\ldots 7.44$$

and,

$$0.04733 = 0.007354 \ln \frac{mC_o(1-K_o)\alpha_2 R_6^b}{DK_o} \quad \ldots\ldots 7.45$$

which gives:

$$\frac{mC_o(1-K_o)\alpha_2 R_6^b}{DK_o} = 623.87 \quad \ldots\ldots 7.46$$

If

$$\frac{mC_o(1-K_o)}{K_o} = 1.7 \text{ for 25\% Cr in iron,}$$

and $D = 3 \times 10^{-3}\ cm^2 s^{-1}$
then

$$\alpha_2 R_6^b = 1.10095 \quad \ldots\ldots 7.47$$

The same argument may be applied to the regression equation for λ_1 at 14 mm from the chill zone:

$$\lambda_1\ (14mm) = 0.09485 + 0.01480 \ln\frac{1}{\Delta T} \quad \ldots\ldots 7.48$$

which gives

$$\frac{D}{\alpha_1 R_{14}^a} = 0.01480 \quad \ldots\ldots 7.49$$

Thus:

$$0.09485 = 0.01480 \ln \frac{mC_o(1-K_o)\,\alpha_2 R_{14}^b}{DK_o} \quad \ldots\ldots 7.50$$

giving,

$$\frac{mC_o(1-K_o)\,\alpha_2 R_{14}^b}{DK_o} = 606.89 \quad \ldots\ldots 7.51$$

and

$$\alpha_2 R_{14}^b = 1.07098 \quad \ldots\ldots 7.52$$

The ratio of the growth term at 6mm to the growth term at 14mm is:

$$\frac{\alpha_2 R_6^b}{\alpha_2 R_{14}^b} = \frac{1.10095}{1.07098}$$

$$= 1.02798 \quad \ldots\ldots\ldots\ldots\ldots\ldots\ldots\ldots \quad 7.53$$

If **b** is assumed to have the value found from the statistical analysis in the previous section, i.e. **0.08**, then the ratio of growth rates at these two distances becomes:

$$\frac{R_6}{R_{14}} = (1.02798)^{1/0.08}$$

$$= 1.4119 \quad \ldots\ldots\ldots\ldots\ldots\ldots\ldots \quad 7.54$$

This suggests that the growth rate drops **1.412** times as the solidification front proceeds from 6 mm to 14 mm from the chill zone

At this stage, the exponential terms in the regression equations for grain width (equations **7.39** and **7.40**) should be reconsidered. It was found that the numerator of the exponential term decreased **1.395** times, as the point of measurement moved from 6 mm to 14 mm. This value is very close to the reduction in growth rate found between the same lines of measurement which was **1.412**. So it can be assumed that the reduction in the numerator of the exponential term arises from the change in the growth rate and the equation for grain width can be reformulated as:

$$gw = \frac{D}{\beta_1} \exp\left[\frac{-mC_o(1-K_o)\beta_2 R}{DK_o\Delta T}\right] \ldots\ldots\ldots\ldots\ldots\ldots 7.55$$

As can be seen, the R term in the coefficient on the right hand side of the equation was omitted because, empirically, the value of this coefficient was found to be insensitive to the change in the distance from the edge of the ingot. Even if the R term were included its exponent would be small enough to make its value approach unity.

If the regression equation for λ_1 is considered again, and when equation **7.44** is divided by equation **7.49** the following result is obtained.

$$\frac{R_{14}^{a}}{R_{6}^{a}} = \frac{0.007354}{0.01480}$$

$$= 0.49689 \quad \ldots\ldots\ldots\ldots\ldots\ldots\ldots\ldots \quad 7.56$$

It was shown above that

$$R_6 = 1.4119\ R_{14} \quad \ldots\ldots\ldots\ldots\ldots\ldots\ldots\ldots 7.54$$

Then by substitution

$$\frac{R_{14}^{a}}{(R_{14} * 1.4119)^{a}} = 0.49689 \quad \ldots\ldots\ldots\ldots\ldots\ldots\ldots 7.57$$

When the equation **7.57** is solved for **a**, it is found that

$$a = 2.0276 \approx 2.0$$

So, the general equation for λ_1 can be rewritten as:

$$\lambda_1 = \frac{D}{\alpha_1 R^2} \cdot \ln \frac{mC_o(1-K_o)\alpha_2 R^{0.08}}{D \cdot K_o \cdot \Delta T} \quad \ldots\ldots\ldots\ldots\ldots\ldots\ldots 7.58$$

It should be noted that equations **7.55** and **7.58** are sensitive to two main parameters:

(i) superheat
(ii) growth rate

Growth rate is also a function of superheat and distance from the chill zone in this case. However the assumption that, at a given distance from the chill zone, the growth rate stays constant for different amounts of superheat, might introduce a small error in the results when these equations are applied to other alloy systems. As could be noticed, with the data obtained from this work, it was the change in growth rate that was calculated, not the growth rate itself. Therefore, the possibility still exists that these equations could reflect the influence of growth rate on the structure which may change with the degree of superheat at a given distance from the chill zone.

Constants α_1 and α_2 for primary arm spacing, and β_1 and β_2 for grain width are believed to act as correction factors, compensating for the actual growth rate, the thermal gradient and the constitutional term which could not be measured or calculated precisely in this work

However, the strength of these quasi-empirical equations comes from the fact that they have proved to hold over a casting temperature range of 150°C and they reflect the change in macro-grain size and in primary arm spacing with the change in the distance from the chill zone.

These equations suggest that when the constitution of the alloy, the shape, size and mould material as well as the cooling medium are kept constant, the degree of superheat influences the macrostructure and microstructure as follows:

(i) As the superheat is decreased, the macro grain

size gets smaller following an inverse exponential curve

(ii) As the superheat is decreased, the primary dendrite arm spacing gets bigger following a logarithmic curve

(iii) At a given superheat the growth of a macro grain is determined by the growth rate of the dendrites making up that specific grain, which becomes a function of the distance of the solid-liquid interface from the chill zone

(iv) At the limit, when the rate of heat extraction is very low (and the growth rate is also low), which is usually the case as $\Delta T \rightarrow 0$, the coarsest microstructure is obtained. However this is also the condition for the proportion of the equiaxed zone to approach 100%. Thus there is a price to be paid for obtaining an equiaxed zone by decreasing the amount of superheat. This is in the form of a coarser microstructure. This was also obvious in the microstructures displayed in Figure **6.30** for AISI310S.

(v) At a given degree of superheat, grain width and primary dendrite arm spacing respond differently to changes in the constitution of the alloy. If the constitutional parameter $\left(\frac{mC_o(1-K_o)}{K_o}\right)$ increases, the grain width gets smaller. However the dendritic arm spacing tends to coarsen. Thus if a refined macrostructure is to be obtained by adding constitutional supercooling promoters, a coarser microstructure seems to be unavoidable, as the above equations suggest.

As can be seen from Figures **7.11** and **7.12**, when plotted, the relationship between grain width/primary arm spacing and superheat is very similar to the curve obtained by ploting an equation of the general form:

$$y = \frac{1}{e^{x}\, lnx} \qquad \text{.....7.61}$$

with dimensionless coordinates. The only difference between the two relationships is that the former approaches unity as **x** or **1/superheat** approaches infinity whereas the latter approaches zero.

The physical explanation of the behaviour of the former curve is that at the limit which is 0°C superheat one grain consists of only one single dendrite arm. Equation **7.59** provides the means to support this physical reality: the exponential and logarithmic term on the right hand side of the equation contains the growth rate term **R** which also decreases as the superheat is decreased. The change in **R** counterbalances the change in ΔT to such a degree that equation **7.59** approaches unity as ΔT approaches 0°C.

The similar shapes of the experimental data curve and that of the general mathematical equation stated above strongly suggest that the proposed quasi-empirical relationship (equation **7.59**) can be used to express the relationship between grain width and primary dendrite arm spacing.

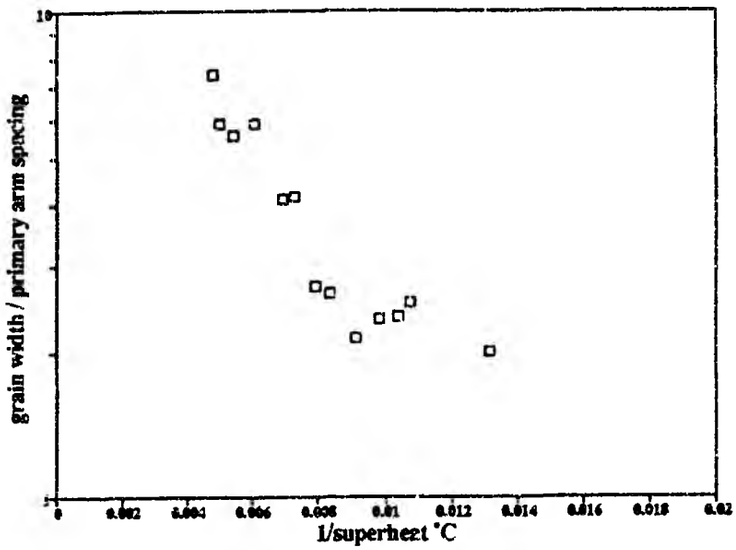


Figure 7.11 The plot of grain width/primary dendrite arm spacing against 1/superheat using the experimental data of this work

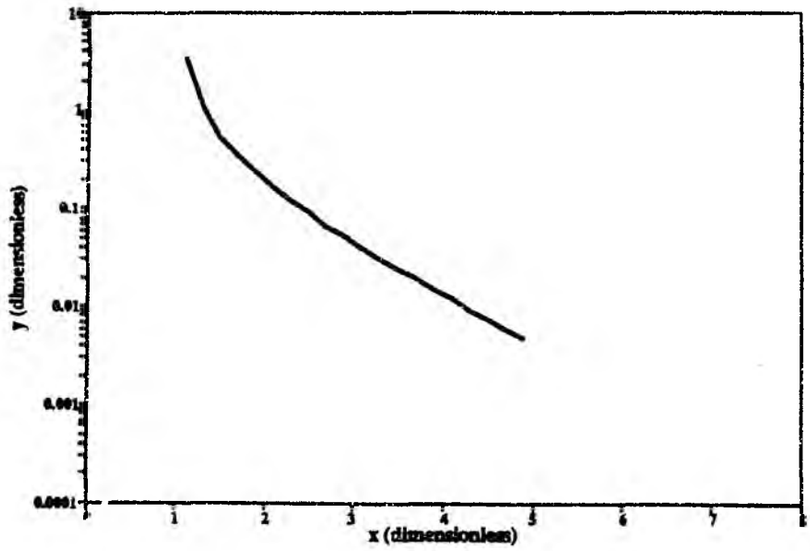


Figure 7.12 The plot of the equation $y = \frac{1}{e^x \ln x}$ with dimensionless coordinates

7.5 The Influence of Additions on the Macro- and Microstructure of AISI310S Stainless Steel

The information compiled during the course of this work and the quasi-empirical model proposed for the solidification structure of AISI310S steel enable a clearer understanding as to why the additions made to the melt to refine the macrostructure had no effect on the microstructure. Misch metal and zirconium additions have the potential to refine the macrostructure of the AISI310S steel within a certain casting temperature range. This implies that their potential to promote constitutional supercooling is not big enough to show significant effects where the drop in thermal gradient becomes the main controlling factor in the development of structure. If a stronger constitutional supercooling promoter could be found for this type of steel, it could be effective over a wider temperature range. The same phenomenon was also observed by Fiegenschuh[166] who also studied the effect of cooling rate on the effectiveness of additions and Gautschi[317] who observed that the refining effect was lost when the cooling rate was slower.

It will be appreciated that the major effect of misch metal and zirconium additions was the significant change in growth pattern of the columnar grains of the steel. Misch metal appears to increase the grain width ratio in the casting temperature range 1535-1551°C, due to an increase in the nucleation rate of austenitic grains.

Figure **6.30** clearly indicates that as the grain refinement progresses by the addition of misch metal the microstructure gets coarser. This phenomenon confirms the predictions of the quasi-empirical model suggested in section **7.3**.

The sudden drop observed in grain refinement within a very small concentration range of rare earth additions could be related to the fact that, as the concentration of rare earths approaches the solid solubility limit, their activity gets closer to unity, and at the limit it is equal to unity where the addition tends to form compounds with iron minimizing its constitutional effect. A further increase in its concentration provides excess rare-earth which contributes to constitutional supercooling creating the same refining effect again. This phenomenon is typical of cases where the addition promotes constitutional supercooling. The same effect was observed in Fiegenschuh's work[186] where he added rare-earths and misch metal to G-X 15CrNiSi2520 which is constitutionally similar to AISI310S. He related this phenomenon to the grain growth inhibiting effect of the rare earths, i.e. up to a certain concentration of RE, a thin film formed around the grains inhibiting their further growth. However when the concentration reached a certain level it was more favourable for the RE to form a stable compound and therefore, the grain growth inhibiting effect disappeared. As the concentration was increased even further the excess RE reproduced the same effect as it did in the ppm concentration levels. The constitutional supercooling approach and Fiegenschuh's theory may be related as both have the potential to explain the effect. However the relative increase observed in the grain width ratio with addition of misch metal supports the constitutional supercooling mechanism.

This change was more significant in a certain range of residual Ce and La concentration (about 100 ppm). As pointed out in section 7.2, if the nucleation rate is increased at a given growth rate, the grains start very thin and then get thicker at a rate controlled by the rate of increase of the primary dendrite arm spacing.

This conclusion is in good agreement with the empirical findings of other researchers. Almost all the researchers agree that as the constitutional supercooling or Tarshis parameter increases, the as-cast grain size tends to get smaller, whereas as was mentioned in the previous section, Okamoto et al[314] showed that the primary arm spacing tends to get larger for the alloy systems: Fe-Ni, Fe-Si, Fe-P and Fe-C.

Using equations **7.55** and **7.58**, a mathematical expression can now be derived to relate grain width measured at any distance from the chill zone of an ingot cast with a specific superheat to the primary arm spacing measured at the same point as follows:

$$\frac{gw}{\lambda_1} = \frac{\alpha_1 R^2}{\beta_1} \frac{1}{\left[\exp \frac{mC_o(1-K_o)\beta_2 R}{DK_o\Delta T} \ln \frac{mC_o(1-K_o)\alpha_2 R^{0.08}}{DK_o\Delta T}\right]} \quad \ldots\ldots 7.59$$

simplifying this relationship:

$$gw = \lambda_1 \left(\frac{A}{e^{B/\Delta T} \ln \frac{C}{\Delta T}} \right) \quad \ldots\ldots 7.60$$

where $A = \frac{\alpha_1 R^2}{\beta_1}$

$B = \frac{mC_o(1-K_o)\beta_2 R}{DK_o}$ and

$C = \frac{mC_o(1-K_o)\alpha_2 R^{0.08}}{DK_o}$

The relative increase in the grain width ratio with misch metal additions suggests an increase in the nucleation rate of austenitic grains especially in the regions closer to the mould wall, but there seems to be no growth inhibiting process in operation at least in the direction parallel to the mould surface. The structure of the columnar zone obtained in the casting temperature range 1535-1555°C with misch metal addition is similar to that of the base metal cast between 1475 and 1500°C. It should be noted that below those temperatures the grain width ratio of the base metal tends to approach unity again due to the decrease in the growth rate.

As far as the refinement of the macrostructure is concerned, the limit for a single columnar grain is to consist of only one primary dendrite arm. Thus, further refinement in the width of columnar grains does not seem possible once they reach that single dendrite arm size which actually seems to be coarser than those comprising multiple primary dendrite arms. Once they reach that single dendrite arm size, the contribution of additions to constitutional supercooling (in the case of misch metal and zirconium) gets dwarfed by the drastic contribution of a lower degree of superheat, at which the equiaxed zone starts to form with an exponential speed and dominates the structure as the equations suggest.

The effect of zirconium addition in the form of either FeSiZr or pure Zr on grain width ratio is not as significant as that of misch metal additions. However, Zr additions reduced the grain width by about 50% in certain casting temperature ranges, which suggests a grain growth restricting effect is in operation together with an increase in the nucleation rate.

All these observations suggest that refinement of macrostructure via the constitutional supercooling route brings about a coarser microstructure. The secondary arm spacing appears to show a certain refinement in parallel to the refinement of macrograins, but the change remains within the error range of secondary arm measurements. The comparison should be made within a larger range of variation of growth parameters in order to see if a significant trend exists.

7.6 Effect of Macrostructural Changes on the Mechanical Properties of the As-Cast AISI310S Stainless Steel

The expected, and desired, result of grain refinement would be an improvement in tensile strength or elongation. However this does not occur in all cases. Refining techniques applied to plain carbon and medium alloy steels have produced adequate refinement of the cast grain size, but have failed to result in an improvement in mechanical properties. In fact, these steels have been embrittled by the addition of grain refining inoculants[221]. Other studies on the solidification behaviour of medium alloy steels have indicated that the regions of castings that solidify with a columnar structure have improved strength and ductility compared to portions of the casting with an equiaxed structure.

Flemings[318], and Church et al[319] related the improved properties of columnar structures to the solidification conditions under which they formed rather than the structures themselves. A columnar type of solidification is generally favoured by a steep thermal gradient This steep gradient also provides good feeding conditions for the solidifying metal and results in reduced microshrinkage, and improved strength. This approach also explains the observations of the present work, that as the superheat is decreased the columnar grain size is refined but the strength of the material decreases. However the ingot with an equiaxed zone of 70% showed superior mechanical properties in contrast to observations by previous researchers.

This phenomenon can be related to the following factors:

7.6 Effect of Macrostructural Changes on the Mechanical Properties of the As-Cast AISI310S Stainless Steel

The expected, and desired, result of grain refinement would be an improvement in tensile strength or elongation. However this does not occur in all cases. Refining techniques applied to plain carbon and medium alloy steels have produced adequate refinement of the cast grain size, but have failed to result in an improvement in mechanical properties. In fact, these steels have been embrittled by the addition of grain refining inoculants[221]. Other studies on the solidification behaviour of medium alloy steels have indicated that the regions of castings that solidify with a columnar structure have improved strength and ductility compared to portions of the casting with an equiaxed structure.

Flemings[318], and Church et al[319] related the improved properties of columnar structures to the solidification conditions under which they formed rather than the structures themselves. A columnar type of solidification is generally favoured by a steep thermal gradient. This steep gradient also provides good feeding conditions for the solidifying metal and results in reduced microshrinkage, and improved strength. This approach also explains the observations of the present work, that as the superheat is decreased the columnar grain size is refined but the strength of the material decreases. However the ingot with an equiaxed zone of 70% showed superior mechanical properties in contrast to observations by previous researchers.

This phenomenon can be related to the following factors:

(i) the ingots were cast under argon so there was little likelihood of gases being absorbed in the metal and of macro- or micro-porosity forming in the ingots.

(ii) however in the presence of a small amount of micro-porosity the previous researchers' explanation for better properties with coarser columnar grains needs to be either modified or applied only to sand-castings and/or castings made without a protective atmosphere.

(iii) a possible explanation may stem from the fact that columnar structure is highly anisotropic. However as the columnar grain width gets smaller, so does the degree of anisotropy as shown in Figure **6.50**. There is also a shape effect in that columnar grains have a high aspect ratio as shown in Figure **7.13**. As described in Chapter 6, tensile test pieces were prepared from two orientations perpendicular to each other and to the direction of heat flow. The alignment of the grains in these test pieces is shown schematically in Figure **7.14**.

These schematic figures explain the difference in tensile test results between samples taken in two directions. In specimen A, the grains tend to align themselves at 45° to the tensile axis direction in order to minimize the shear stresses acting on the test piece. In specimen B this need is minimal, since the alignment of the grains in the test piece is such that the tensile axis and the slip planes (the grain boundaries in this case) are already almost parallel to each other.



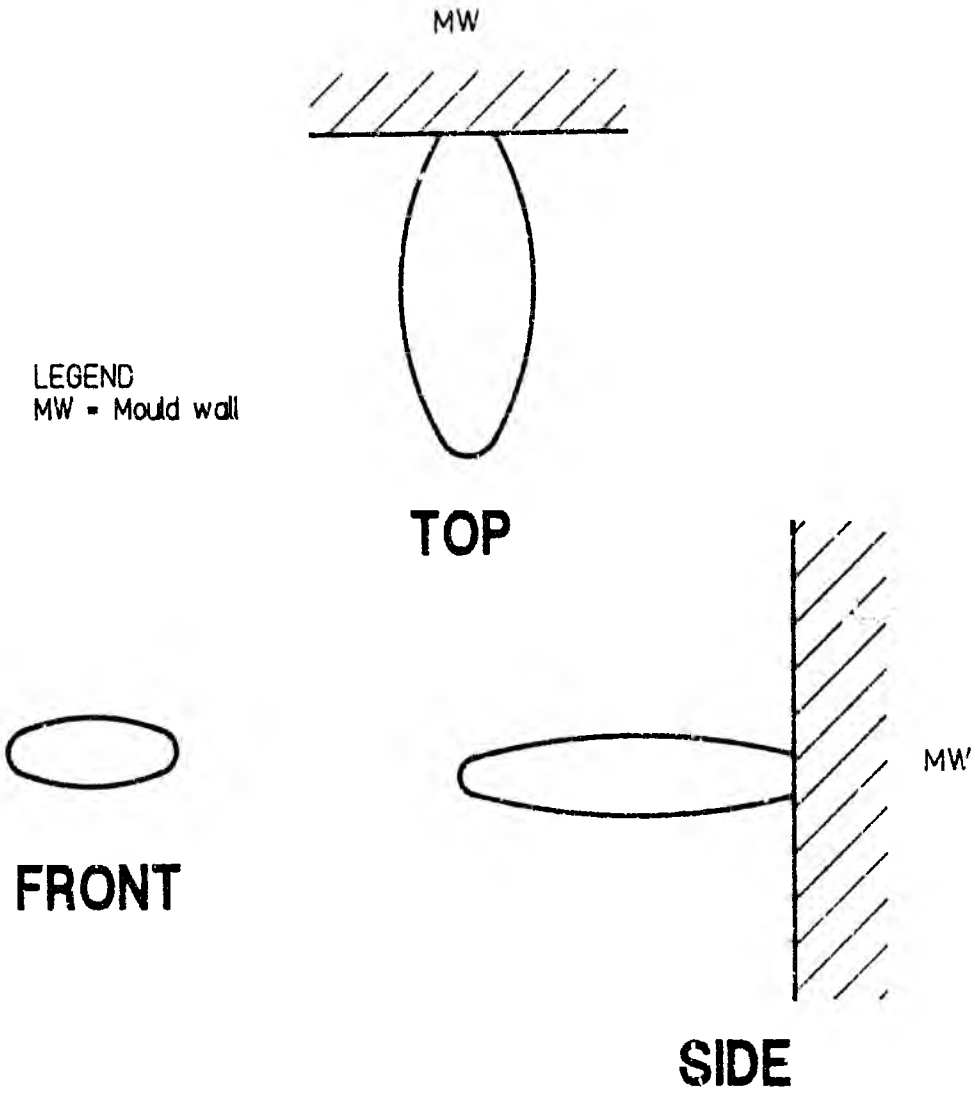



Figure 7.13 Schematic representation of the sections of a columnar grain

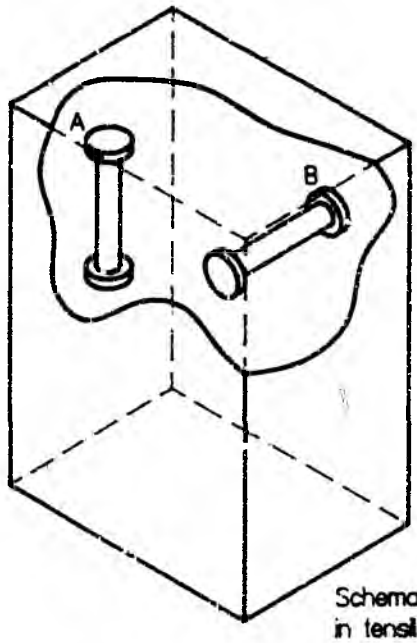

Schematic alignment of the columnar grains in tensile test pieces.

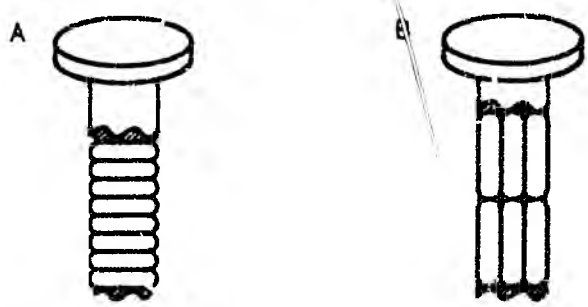

Ingot with coarse columnar grains.

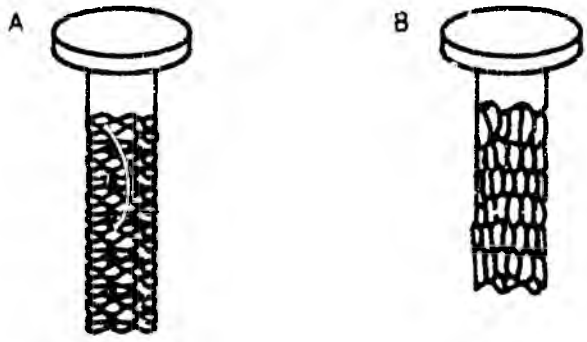

Ingot with fine columnar grains.

Figure 7.14 Schematic representation of the alignment of columnar grains in tensile test pieces

Thus the specimen starts to flow with minimal effort and the tensile strength is relatively low compared to that of specimen A. This difference in the mode of deformation also shows itself in the shape of the fractured surface as shown schematically in Figure **7.15**, and in the photographs of Figure 6.15. Now, as the columnar grain size and the directionality of the grains decrease, this difference in the mode of deformation and fracture also becomes smaller as it was observed in Figures **6.50** and **6.51**. Thus grain size and shape may become the controlling factors in the deformation and fracture mode and in the degree of anisotropy in deformation once the macro- and micro-porosities are brought down to minimal levels. If there is no grain boundary at all (single crystal), then the determining factor would become the strength of the regions between the neighbouring dendrite arms (in the case of castings), i.e. the primary and/or secondary arm spacing play the dominant role in the deformation mode.

This is analogous to a chain with a weak link. In this case the weak link in order of increasing strength may be one of the following:

(i) microporosity
(ii) grain boundaries
(iii) the regions between dendrite arms when only one dendrite is present

In the case of equiaxed structures, a large grain boundary area and an isotropic structure contribute to the higher yield and tensile strengths, and there is almost no difference between the test results obtained in different directions. However, this does not mean that one would always get better strengths with equiaxed structures.


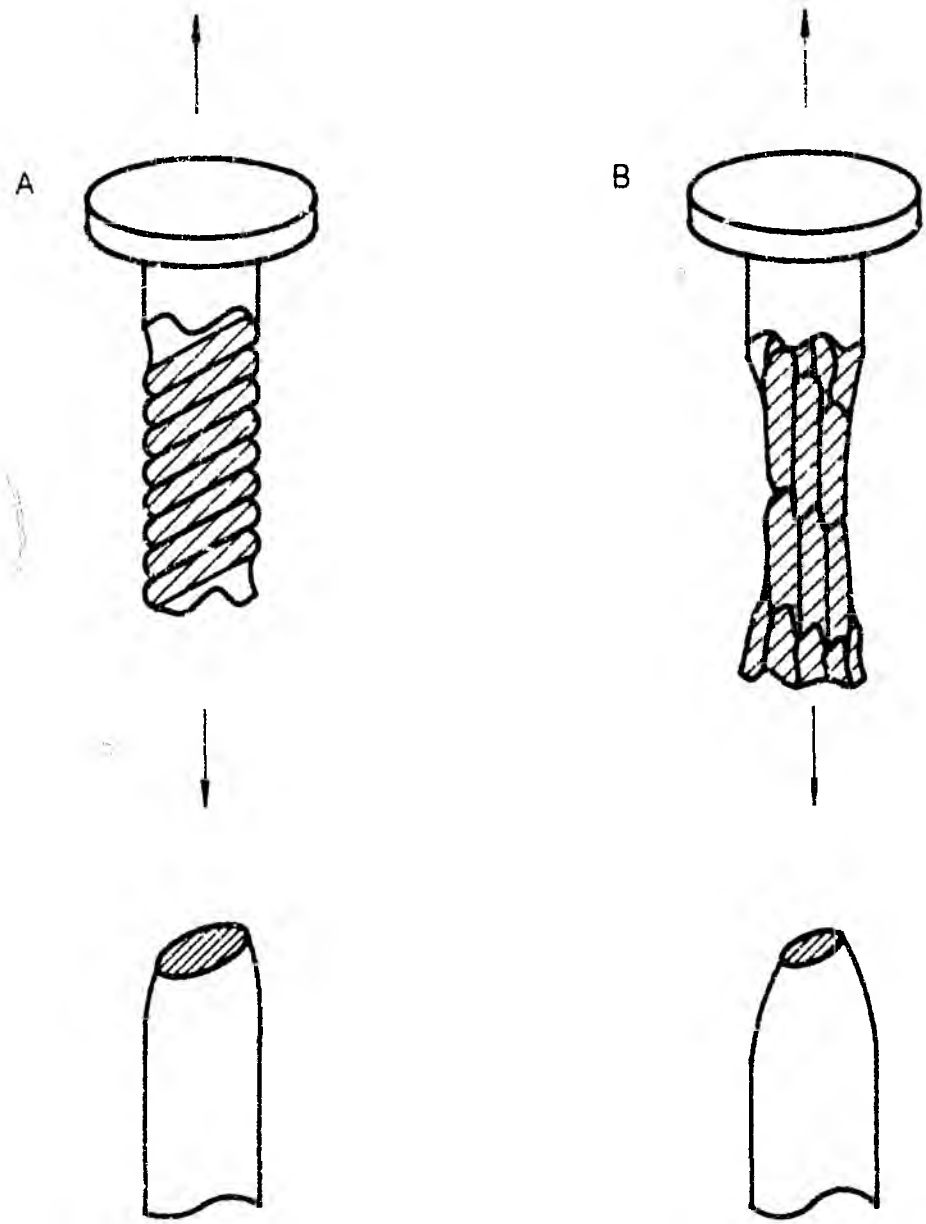


Figure 7.15 Schematic representation of the deformation modes for tensile test pieces A and B and the corresponding fracture surfaces.

If the grain size is coarse as shown in Figure **7.16**, the strengths would most probably deteriorate due to a smaller grain boundary area. The isotropic behaviour of this equiaxed structure would also facilitate the slide of grains over neighbouring grains. They would not be pulled apart as was the case with the coarse columnar structures of tensile specimens cut in direction "A". Thus, the grain size effect is reversed in equiaxed structures. Strength decreases as the grain size is increased, which is opposite to what happens in columnar structures. This approach also explains the results of previous works, obtained with equiaxed materials which gave lower strengths than materials with columnar structures. Their equiaxed structures most probably were not fine enough to give better strength values.

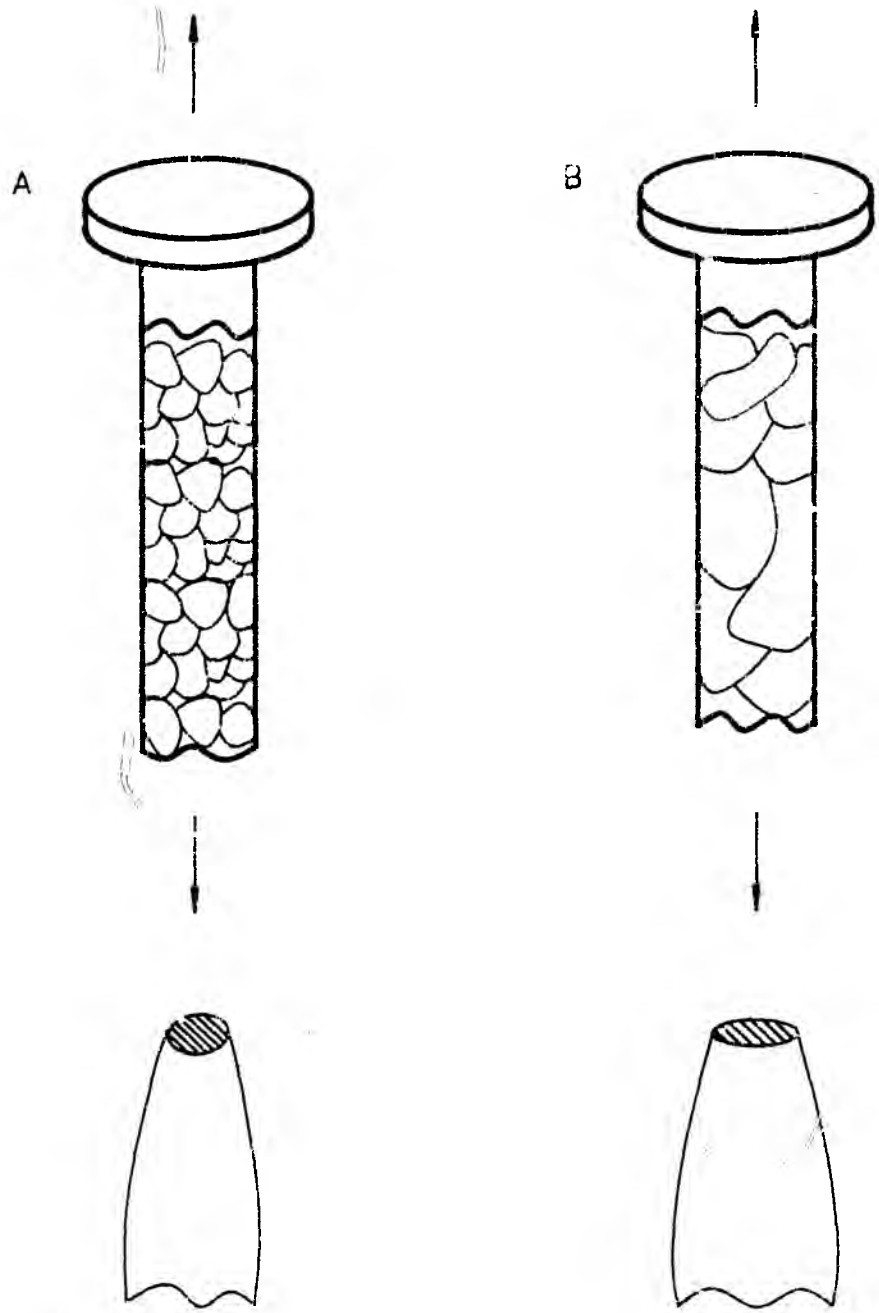

a) A fine equiaxed structure

b) A coarse equiaxed structure

Figure 7.16 **Schematic representations of the deformation mode for tensile test pieces cut from cast ingots with equiaxed structures**

8. CONCLUSIONS

From the experimental results obtained in this study and the quasi-empirical solidification model developed, the following major conclusions can be drawn with regard to the changes in macrostructure and microstructure of AISI310S stainless steel produced under different conditions.

8.1 At cooling rates exceeding a certain value, AISI310S goes through a peritectic reaction during solidification. The cooling rates necessary for peritectic transformation were estimated from the secondary arm spacing of the cast structures. These cooling rates were estimated for the first time to range between about 1400 and 1500°Cs^{-1} . The solidification process may then be expressed as: liquid $\rightarrow \delta$ + liquid $\rightarrow \gamma$. Thus under certain conditions AISI310S may transform to delta ferrite first followed by transformation to austenite. This was evidenced by the presence of δ grain boundaries in austenite. At very high casting temperatures primary δ grain boundaries were not observed due to the remelting of the initial δ chill grains and a reduction of the chilling capacity of the mould walls.

8.2 The proportion of the equiaxed zone increased with decreasing alloy superheat. Plots of proportion equiaxed zone against natural logarithm of superheat produced a linear relationship which could be expressed by the equation:

$$\% \text{ equiaxed zone} = 244.5 + 49.4 \ln\frac{1}{\Delta T}$$

where ΔT = superheat in °C.

A quasi-empirical equation was developed, which expresses the strong link between the kinetics of formation of the equiaxed zone and constitutional supercooling, in the following form.

$$\% \text{ equiaxed zone} = \frac{D}{aR} \ln\left[\frac{mC_o(1-K_o)R}{K_o D\Delta T}\right]$$

8.3 The columnar grain size decreased in an inverse exponential fashion with decreasing superheat. The relationship could be expressed by an equation of the type:

$$gw = e^{\left(a+\frac{b}{\Delta T}\right)}$$

8.4 Plots of primary dendrite arm spacing against natural logarithm of the reciprocal of superheat were linear indicating that the primary dendrite arm spacing increased logarithmically with decreasing superheat.

The mathematical relationship between these two variables was as follows:

$$\lambda_1 = c + d \ln\frac{1}{\Delta T}$$

It is evident from the mathematical relationships in 8.3 and 8.4 that gw and λ_1 responded differently to superheat. While gw increased with superheat λ_1 decreased.

8.5 The growth rate of a macro grain at a given superheat was determined by the growth rate of the dendrite making up that specific grain. The growth rate of the dendrite was a function of the distance of the solid-liquid interface from the chill zone. The widening rate of columnar grains at different distances from the chill zone was not constant. This phenomenon was described by the term **"grain width ratio"** which was defined as the ratio of grain widths in flat sections at different distances from the chill zone. This ratio was found to approach unity at high and low superheats as a result of the competition between grain nucleation and growth.

8.6 The coarsest microstructure was obtained when the rate of heat extraction was very low, which is usually the case as $\Delta T \rightarrow 0$. However this is also the condition where the proportion of the equiaxed zone approaches 100%. Thus as the proportion of the equiaxed zone increased, due to a decrease in superheat, the primary interarm spacing increased.

8.7 At a given degree of superheat, the grain width and primary dendrite arm spacing responded differently to changes in the constitution of the alloy. When the constitutional parameter (P in equation **4.1**) increased, the grain width decreased. However the dendritic arm spacing tended to coarsen. Thus if a refined microstructure is to be obtained by adding constitutional supercooling promoters, a coarser microstructure appears to be unavoidable. It has been seen that relatively coarse microstructures were obtained with Misch Metal additions which

refined the macrostructures by up to 50%. This effect could be attributed to their ability to provide constitutional supercooling in this type of steel.

8.8 A mathematical expression was derived from the experimental data as follows:

$$gw = \lambda_1 \frac{A}{e^{\frac{B}{\Delta T}} \ln \frac{C}{\Delta T}}$$

where gw is the grain width, λ_1 is primary dendrite arm spacing, and the terms A, B and C contain the growth rate, diffusion rate and constitutional parameters as described in detail in equation **7.47** in Section **7.5**. This equation could describe the changes which took place in the macrostructure and microstructure of the AISI310S stainless steel when cast over a range of 150 degrees of superheat. It strongly suggests that a link between macrostructure and microstructure can be established universally by an equation of this form if the dominating solidification mechanism is constitutional supercooling. However it requires further experimental evidence to develop a general expression which would describe all the alloy systems which solidify under conditions of constitutional supercooling.

8.9 The improved tensile properties obtained in coarse columnar structures and the difference between specimens taken in different orientations could be explained by taking grain size and shape into account. Grain size and shape may become the

controlling factors in the deformation and fracture mode and in the degree of anisotropy once the the macroporosity and microporosity are reduced to the minimum. If there is no grain boundary at all (single grain), then the determining factor would become the strength of the regions between the primary dendrite arms. In the case of equiaxed structures, a large grain boundary area and the isotropic structure contribute to the increase in the yield and tensile strengths. There was almost no difference between the test results obtained from specimens taken from equiaxed ingots in two different orientations.

8.10 The shape of the fracture surfaces of the tensile samples revealed that as the grain size decreased, the deformation became more uniform, and it was almost completely isotropic for the ingot with equiaxed structure. Additions of Misch Metal and Zr resulted in more uniform deformation.

8.11 Improved tensile properties were obtained in the as hot rolled condition due to the grain refining effect of the Misch Metal and FeSiZr additions on the steel.

Regression analyses carried out on the results of the hot rolled tensile and impact properties gave the following equations:

$$\sigma_{YS} = 170 + 42.2\ d^{-1/2}$$

$$\sigma_{TS} = 431.2 + 46.1\ d^{-1/2} \quad \text{or}$$

$$\sigma_{TS} = 56.2 - 13.2d + 2.2d^2$$

$$RA = 81.9 - 33.0 + 18.5d^2$$

$$\text{Impact Energy (J)} = 351.3 + 26.6d - 165.75d^2$$

8.12 Cold rolled AISI310S steel with smaller grain sizes in the hot rolled condition showed a smooth edge and no edge cracking while coarse grained material exhibited rough edges and edge cracking upon cold rolling.

The objectives of this study were to examine the influence of chemical grain refining of AISI310S on its macrostructure, its microstructure and its mechanical properties. It is evident that the primary objectives have been met and some useful relationships relating to the solidification, structure and properties of this alloy have been developed.

These studies also revealed an interesting relationship between superheat and structure which was investigated in some detail.

REFERENCES

1. Hawbolt, E.B., Weinberg, F. and Brimacombe, J.K., **"Influence of Hot Working on Internal Cracks in Continuously Cast Steel Billets"**, Metallurgical Transactions B, vol.10B, June 1979, pp 229-236.

2. Wolf, M., **"Strand Surface Quality of Austenitic Stainless Steels: Part 1 Macroscopic Shell Growth and Ferrite Distribution"**. Ironmaking and Steelmaking, vol 13, No.5, 1986, pp 248-257.

3. Wolf, M., **"Strand Surface Quality of Austenitic Stainless Steels: Part 2 Microscopic Solidification Structure"**, Ironmaking and Steelmaking, vol 13, No.5, 1986, pp 258-262.

4. Kinoshita, K., Yoshii, Y., Kitaoka, H., Kawaharada, A., Nishikawa, K., and Tanigawa, O., **"Continuous Casting of High Alloy Steels"**, Journal of Metals, March 1984, pp 38-43.

5. Ward, R.G., **"Effect of Annealing on the Dendritic Segregation of Manganese in Steel"**, Journal of the Iron and Steel Institute, vol.203, No.9, 1965,p 932.

6. Flemings, M.C., **"Application of Solidification Theory to Large Castings and Ingots"**, ISI Publication No.110, Iron and Steel Institute, 1967, pp 277-288.

7. Melford, D.A., and Granger, D.A., **"Relationship Between Microsegregation and Macrostructure in Killed Steel Ingots"**, ISI Publication No. 110, Iron and Steel Institute, 1967, pp 289-294.

8. Weinberg, F., and Buhr, R.K., **"Solidification Studies of Steel Castings"**, ISI Publication No.110, Iron and Steel Institute, 1967, pp 295-304.

9. Charles, J.A., **"Influence of non-Metallic Inclusions on Solidification of Steel"**. The Solidification of Metals, ISI Publication No.110, 1968, pp 309-312.

10. Chalmers, B., **"The Structure of Ingots"**, Journal of Australasian Inst. of Metals, Vol.8, 1063, pp 255-263.

11. Jackson, K.A., Junt, J.D., Uhlmann, D.R. and Seward, T.P., **"On the Origin of the Equiaxed Zone in Castings"**, Transactions of the Metallurgical Society of AIME, Vol.236, February 1966, pp 149-153.

12. Cole, G.S. and Bolling, G.F., **"Importance of Fluid Motion During Ingot Solidification"**. The Solidification of Metals, ISI Publication No.110, London 1968, pp 323-329.

13. Murakami, K. and Okamoto, T., **"Formation of Equiaxed Zone in Castings"**, Metal Science, Vol.18, February 1984, pp 103-111.

14. Southin, R.T., **"Nucleation of the Equiaxed Zone in Cast Metals"**, Transactions of the Metallurgical Society of AIME, Vol.236, February 1967, pp 220-225.

15. Engler, S., and Ellerbrok, R., **"On the Formation of the Equiaxed Zone in Castings"** In : Nieswaag, H. and Shut, J.W. Eds., Procs. of Symposium on "Quality Control of Engineering Alloys and the Role of Metals Science", Delft, 1977, pp 121-129.

16. Ohna, A., Motegi, T., and Soda, H., **"Origin of the Equiaxed Crystals in Castings"**, Transactions of the Iron and Steel Institute of Japan, Vol.11, 1971, pp 18-23.

17. Chadwick, G.A., **"Heterogeneous Nucleation of Metals from Their Melts"**, Metals and Materials, March 1969, pp 77-83.

18. Backerud, L., **"How Does a Good Grain Refiner Work"**, Light Metal Age, October 1983, pp 6-12.

19. Cole, G.S., Casey, K.W., and Bolling, G.F., **"A Practical Method for Identifying Inoculants"**. Metallurgical Transactions, Vol.5, February 1974, pp 407-411.

20. Form, G.W., and Wallace, J.F., **"Solidification of Metals"**, AFS Transactions, Vol.69, 1960, pp 145-156.

21. Uhlmann, D.R., Seward, T.P., and Chalmers, B., **"The Effect of Magnetic Fields on the Structure of Metal Alloy Casting"**, Transactions of the Metallurgical Society of IAME, Vol.236, April 1966, pp 527-531.

22. Tzavaras, A.A., and Brody, H.D., **"Electromagnetic Stirring and Continuous Casting - Achievements, Problems and Goals"**, J of Metals, Vol.36, No.3, March 2984, pp 31-37.

23. Langenberg, F.C., Pestel, G., and Honeycutt, C.R., **"Grain Refinement of Steel Ingots by Solidification in a Moving Electromagnetic Field"**, Transactions of

the Metallurgical Society of AIME, Vol.221, October 1961, pp 993-1001.

24. Johnston, W.C., Kotler, G.R., O'Hara, S., Ashcom, H.V., and Tiller, W.A., **"Grain Refinement via Electromagnetic Stirring During Solidification"**, Transactions of the Metallurgical Society of AIME, Vol.233, October 1965, pp 1856-1860.

25. Birat, J.P., and Chone, J., **"Electromagnetic Stirring on Billett, Bloom and Slab Continuous Casters : State of the Art in 1982"**, Ironmaking and Steelmaking, Vol.10. No 6, 1983, pp 269-281.

26. Lane, D.H., Cunningham, J.W., and Tiller W.A., **"The Application of Ultrasonic Energy to Ingot Solidification"**, Transactions of the Metallurgical Society of AIME. Vol.218, December 1960, pp 985-994.

27. Abramov, O.V., Izotov, A.N., Astashkin, Yu.S., Kryuchkova, G.A., Manokhin, A.I., Markov, A.V., and Taran, V.P., **"Ultrasonic Treatment of Stream of Molten Metal"**, Steel in the USSR, Vol.15, April 1985, pp 168-170.

28. Hiedemann, A., **"Metallurgical Effects of Ultrasonic Waves"**, J. Acoust. Soc. Ameri., Vol.26, 1954, pp 831-842.

29. Crossley, F.A., Fisher, R.D. and Metcalfe, A.G., **"Viscous Shear as an Agent for Grain Refinement in Cast Metal"**, Transactions of the Metallurgical Society of AIME, Vol.221, April 1961, pp 419-420.

30. Wojciechowski, S., and Chalmers, B., **"The Influence of Mechanical Stirring on the Columnar to Equiaxed Transition in Aluminium - Copper Alloys"**, Transactions of the Metallurgical Society of AIME, vol.242, April 1968, pp 690-698.

31. Campbell J., **"Effects of Vibration during Solidification"**, Int. Metals Review, Vol.26, No.2, 1981, pp 71-108.

32. Radhakrishna, K. and Seshan, S., **"Internal Chills - Another Tool to Improve Casting Properties"**, Castings, January 1980, pp 23-26.

33. Ryzhikov, A.A., Chudner, R.V., Gavrilin, I.V. and Starosel'skii, M.A., **"Improvements in the Suspension Casting Process"**, Russian Castings Production, November 1975, pp 457-458.

34. Sentarli, Y. **"Suspension Casting of a High Chromium White Iron"**, MSc. Dissertation, University of the Witwatersrand, Johannesburg, 1985.

35. Forbes, A., **"The Effect of Suspension Casting on the Mechanical and Hot Workability Properties of AISI Type 310 Stainless Steel"**, MSc Thesis, 1987, Dept. of Metallurgy and Materials Eng., University of the Witwatersrand, Johannesburg.

36. Carney, D.J., and Quenean, B.R., **"Solidification of Stainless Steel Ingots"**, The Physical Chemistry of Steelmaking, Cambridge, Massachussets, MIT Press, 1958, pp 209-215.

37. Ryzhikov, A.A., and Mikryukov, R.A., **"Shaped Castings in Suspension Steel"** Russian Castings Production, 1968, pp 241-242.

38. Ryzhikov, A.A., Feigel'son, B.Yu, Roshchin, M.I., and Svetlov, N.P., **"Producing Sound Steel Castings by Complex Solidification Control"**, Russian Castings Production, 1972, p 142.

39. Ivanov, V.T., Zubov, L.A., Grozov, D.P., and Kovshov, V.M., **"Influence of Micro-Chills on the Properties of Carbon Steel Castings"**, Russian Castings Production, 1974, pp 29-30.

40. Borisov, E.S., and Larionov, A.Ya, **"Gating System for Suspension Casting"**, Russian Castings Production, 1974, p 366.

41. Glasson, E.L. and Emley, E.F., **"Heterogeneous Nucleation in the Solidification of Aluminium and Magnesium Alloys"**, ISI Pub., No.110, London 1968, pp 186-195.

42. Crossley, F.A. and Mondolfo, L.F., **"Mechanism of Grain Refinement in Aluminium Alloys"**, J. Inst. Metals, December 1951, pp 1143-1148.

43. Marcantonio, J.A. and Mondolfo, L.F., **"Nucleation of Aluminium by Several Intermetallic Compounds"**, J. Inst. Metals, Vol.98, 1970, pp 23-27.

44. Sicha, W.E., and Boehm, R.C., **"Effect of 0.05-0.4% Titanium on Grain Size and Tensile Properties of 4.5% Copper-Aluminium (No.195)"**, Am. Foundrymen's Assoc., Preprint no. 48-16, 1948, 11pp.

45. Van Lancker, M., **"Metallurgy of Aluminium Alloys"**, William Clowes and Sons Limited, London, 1967.

46. Ganaha, T., Pearce, B.P., and Kerr, H.W., **"Grain Structures in Aluminium Alloy GTA Welds"**, Metallurgical Transactions A, Vol.11A, August 1980, pp 1351-1359.

47. Cole, G.S., Casey, K.W., and Bolling, G.F., **"The Solidification of Inoculated Aluminium Alloys"**, Metallurgical Transactions, Vol.1, May 1970, pp 1413-1416.

48. Dahl, W., Gruhl, W., Burchard, W.G., Ibe, G., and Dumitrescu, C., **"Solidification and Precipitation in Al-Zr Alloys. I. The Effect of Zr on the Cast Structure"**, Z Metallkd., Vol.68, No.2, February 1977, pp 121-127.

49. Morumune, F., Shingu, H., Kobayashi, K., and Ozaki, R., **"The Liquidus Surface of the Al-Ti-B System at the Al Corner"**, Journal of Jpn. Inst. Met., Vol.41, No.5, May 1977, pp 444-450.

50. Hellawell, A., **"Heterogeneous Nucleation and Grain Refinement in Aluminium Castings"**, Int. Conf. on Solidification and Casting, Sheffield, Proceedings, Vol.2, 1979, pp 161-168.

51. Kirby, J.L., and Levy, S.A., **"Grain Refinement of Aluminium Alloys"**, Light Metals, Vol.2, 1978, pp 381-389.

52. Orszagh, V., **"Contribution to the Influence of Microalloys on the Properties of Aluminium Welds"**, Weld. News (Czech), Vol.27, No. 3, 1977, pp 49-53.

53. Kotschi, R.M., and Loper Jr., C.R., **"Grain Refinement in Cast Aluminium Alloys"**, Transactions of the American Foundrymen's Society, Vol.85, 1977, pp 425-430.

54. Nazar, A.M.M., Clyne, T.W., and de Campos Filho, M.P., **"Using Niobium as Grain Refiner for Commercial Aluminium Alloys"** 33rd Congresso ABM (Proc. Conf.), Rio de Janeiro, July 1978, Assoc. Brasileira de Metais, Sao Paulo, 1978, 20 pp.

55. Medana, R., and Serramoglia, G., **"Influence of Impurities and Metallurgical Conditions on the Casting Quality of Alloys G-AlSi6Cu2Mg"**, Gisserei-Prax., Vol.14, July 1978, pp 215-223.

56. Kumar, R., and Siyaramakrishnan, C.S., **"Adventures in Aluminium Alloy Melting Technology"**, Light Metal Age, Vol.36, No.11-12, December 1978, pp 5-14

57. Farrior, G.M., Brillhart, D.C. Sturdevant, R.D. and Lantz, R.A., **"A Method for Calculating Optimum Grain Refiner Additions to Achieve a Desired Grain Size in Aluminium and Aluminium Alloys"**, Light Metals 1980 (Proc. Conf.) Las Vegas, Nev., 24-28 February 1980, Metallurgical Society AIME.

58. Biloni, H., **"Aluminium Transformation Technology and Applications"**, (Proc. Conf.), Puerto Madryn, Chubut, Argentina, 21-25 August 1978, American Soc. for Metals, 1980, pp 1-79.

59. De Ross, A.B., and Mondolfo, L.E., **"Metallurgical Aspects of Casting Aluminium Alloys"** ibid, pp 81-140.

60. Leibov, Yu M., Rozenberg, V.M., and Nefedova, N.A., **"A Comparative Assessment of the Effectiveness of Modification of Aluminium by Complex Additions Based on Transition Metals"**, Nauchn. Tr. Gos. Nauchno Issled. Proektn. Inst. Splavov Obrab. Tsvetn. Met., Vol.59, 1980, pp 12-19.

61. Perepezko, J.H., and Le Beau, S.E., **"Nucleation of Aluminium During Solidification"**, Aluminium Transformation Technology and Applications 1981 (Proc. Conf.), Buenos Aires, Argentina, 24-26 August 1981, American Soc. for Metals, 1982, pp 309-346.

62. Prasad, S.N., Sharan, R., and Ram, M., **"Rare Earth Additions as Grain Refiner to Aluminium Magnesium Alloys"**, Yugoslav International Symposium on Aluminium II - Working, Casting and Finalising (Proc. Conf.), Titograd, Yugoslavia, 21-23 April 1982, pp 133-143.

63. Prasad, S.N., Sharan, R., and Ram, M., **"Tantalum Additions as Grain Refiner to Aluminium Alloys"**, Aluminium, Vol.59, No.3, March 1983, pp 214-215.

64. Elagin, V.I., Zakharov, V.V.,and Rostova, T.D., **"Prospects of Alloying Aluminium Alloys with Scandium"**, Tsvetn, Met., Vol.12, December 1982, pp 96-99.

65. Hidvegi, E., **"The Metallurgical Background of Aluminium Grain Refining"**, Magy.Alum., Vol.20, No.3-4, 1983, pp 73-78.

66. Ershov, G.S., Filatov, G.P., and Kasatkin, A.A., **"The Effect of the Inoculation Temperature on the Properties of AL7 Alloy"**, Liteinoe Proizvod., Vol.2, February 1983,p 28.

67. Krushenko, T.T., Shustrov, A. Yu, and Napromerov, A.A., **"Modifier for Aluminium Alloys"**, Tsvetn. Metall. Nauchno. Tech. Sb., Vol.10, 116-31 May 1983, pp 20-22.

68. Kumar, R., and Sivaramakrishnan, C.S., **"The Influence if Pseudosurfaces on Solidification of Aluminium Alloys"**, Trans. Indian Inst. Met., Vol 36, No.4, Aug-Oct. 1983, pp 298-303.

69. Jones, G.P., **"New Ideas on the Mechanism of Heterogeneous Nucleation in Liquid Aluminium"**, National Physical Lab. Report No. PB84-162114, 1983, 40 pp.

70. Gangulee, A. and Gurland, J., **"Fracture of Silicon Particles in Aluminium-Silicon Alloys"**, Trans. AIME., Vol.236, 1966, pp 263-272.

71. Chadwick, G.A., **"Eutectic Alloy Solidification"**, Prog. Mat. Sci., Vol.12, 1963, pp 97-182.

72. Hunt, J.D., and Jackson, K.A., **"Binary Eutectic Solidification"**, Trans. AIME, Vol.236, 1966, pp 843-852.

73. Jackson, K.A., **"Liquid Metals and Solidification"**, ASM, Cleveland, Ohio, 1958, pp 174-186.

74 Jackson, K.A., **"Growth and Perfection of Crystals"**, ed Doremus, R.H. et al, Wiley and Sons Inc., New York, 1958, p 319.

75. Hellawell, A., **"The Growth and Structure of Eutectics with Silicon and Germanium"**, Progr. Materials Science, Vol.15, 1970. pp 1-78.

76. Tiller, W.A., **"Liquid Metals and Solidification"**, ASM., Cleveland, Ohio, 1958, pp 276-318.

77. Hansen, M. and Anderko, K., **"Constitution of Binary Alloys"**. McGraw Hill, New York, 1958, pp 132-134.

78. Gabriel, J., **"Effect of Antimony Addition on Structure and Mechanical Properties of the Cast Light Alloy GK-ASi7Mg"**, Giesserei, Vol.63, No.10/11, 27 May 1976, pp 311-316.

79. Parkhutik, P.A., Kalashnik, L.D., and Lubenskii, M.Z., **"Modification of Hypereutectic Silumins with Phosphorus and Sodium"**, Met. Sci. Heat Treat., Vol.19, No. 7-8, July-August 1977, pp 713-715.

80. Zhang, Q., Zheng, C., and Han, W., **"The Modification of Al-Si Eutectic Alloys with Rare Earth Elements"**, Acta Metall Sin., Vol. 17, No.2, April 1981, pp 130-136.

81. Efimenko, V.P., Baranov, A.A., Kisunko, V.Z., Bychkov, Yu B., and Prygunova, A.G., **"The Modifying Effect of Certain Microadditives on the Crystallization of Silumins"**, Izv. V.U.Z. Tsvetn. Metall, Vol.6, 1982 pp 86-90.

82. Eshonov, K.K., and Gantsev, I.N., **"Complex Alloy Modification of Alloy AK9"**, Liteinoe Priozvod, No.4, April 1982, pp 35.

83. Wallace, J.F. and Maier, D.R., **"How Inoculation Works"**, Conf. Proc. on the Inoculation Techniques of Gray Cast Iron, AFS., 1980, pp 41-59.

84. Wallace, J.F., **"Effects of Minor Elements on the Structure of Cast Irons"**, Trans. AFS., Vol.83, 1975, pp 363-377.

85. Bader, E.I , **"Investigation of the Mechanism of Modifying Malleable Cast Iron"**, Liteinoe Proizvod, Vol.10, October 1976, pp 9-10.

86. Hughs, T.C.H., **"The Importance and Practice of Inoculation in Iron Castings Production"**, Solidification Technology in the Foundry and Casthouse (Proc. Conf.), University of Warwick, Coventry, 15-17 September 1980, The Metals Society, 1981, paper No.36.

87. Kobayashi, K.F., Hashimoto, S., and Shingu, P.H., **"Nucleation of Aluminium by Aluminium-Titanium (Al_3Ti) in the Aluminium-Titanium System"**, Z. Metallkde., Vol.74, 1083, pp 751-754.

88. Cibula, A., **"The Mechanism of Grain Refinement of Sand Castings in Aluminium Alloys"**, J. Inst. Metals, Vol.76, 1949, pp 321-360.

89. Cibula, A., **"The Grain Refinement of Aluminium-Alloy Castings by Additions of Titanium and Boron"**, J. Inst. Met., Vol.80, 1951-52. pp 1-16. (Paper No.1319).

90. St. John, D.H., and Hogan, L.M., **"Al_3Ti and the Grain Refinement of Aluminium"**, J. Aust. Inst. Met., Vol.22, No.3/4, September-December 1977, pp 160-170.

91. Morumune, F., Shingu, H., Kobayashi, K., and Ozaki, R., **"The Role of TiB_2 Particles on the Grain Refinement of Cast Pure Aluminium"**, J.Jpn. Inst. Light Met., Vol.28, No.2, February 1978, pp 70-78.

92. Pearson, J., and Birch, M.E.J., **"The Effect of the Titanium:Boron Ratio on the Efficiency of Aluminium Grain Refining Alloys"**, Light Metals 1979, Carbon Technology, Cast Shop Technology, Environmental Control Technology (Proc. Conf), Metallurgical Society AIME, New York, N.Y. 1979, pp 757-770.

93. Gokhstein, M.B., and Morozov, Ya I., **"The Modifying Action of Titanium on the Macrostructure of Aluminium"**, Tr. Vses. Nauchno-Issled. Proektn. Inst. Alyum, Magn. Electrod. Prom-st., Vol 99, pp 42-45.

94. Reif, W., and Schneider, W., **"Interpretation of the Process in the Grain Refining of Aluminium Melts with Aluminium-Titanium-Boron Pre-alloys"** Proc.DGM-VDG Joint Committee, Metal Science Problems of Foundry Practice, 6 October 1977, Deusch. Tes. Metallkd. Fachber, Vol.50, June 1978, 11 pp.

95. Nefedova, N.A., Liebov, Yu M., and Rozenberg, V.M., **"The Effect of the Structure of an Aluminium-Titanium 5 Boron 1% Alloy and of the Conditions of its Solidification on the Effectiveness of Modifying Aluminium"**, Nauchn. Tr. Gos. Nauchno Issled. Proektn. Inst. Splavov Obrab. Tsvetn. Met. Vol.63, 1980, pp 37-46.

96. Arnberg, L., Backerud, L., and Klang, H., **"Possible Grain Refining Mechanisms in Aluminium as a Result of Addition of Master Alloys of the Al-Ti-B Type"**., Grain Refinement and Castings in Welds, (Proc. Conf.), St. Louis, Mo., U.S.A., 25-26 October, 1982, The Metallurgical Society/AIME, 1983, 165-181.

97. Rombout, H., **"Recent Developments in the Grain Refinement of Aluminium by Addition of Master Alloys of the Al-Ti-B Type"**, Int. Conf. on Aluminium-85 (INCAL), (Proc. Conf.), New Delhi, India, 30 October - 2 November 1985, Indian Inst. of Metals, 1985, pp 209-218.

98. Kim, C.B., and Heine, R.W., **"Fundamentals of Modification in the Aluminium-Silicon System"**, J. Inst. Met., Vol.92, 1963-64, pp 367-377. (Paper No. 2256).

99. Davies, V. de L., and West, J.M., **"Factors Affecting the Modification of the Aluminium-Silicon Eutectic"**, ibid, pp 175-180.

100. Mondolfo, L.F., **"Eutectic Solidification"**, J. Inst. Metal., Bull. Met. Rev., Vol.94, 1966, pp 399-400.

101. Shu-Zu, Lu and Hellawell, A., **"The Mechanism of Silicon Modification in Aluminium-Silicon Alloys : Impurity Induced Twinning"**, Metallurgical Transactions A, Vol.18A, October 1987, pp 1721-1733.

102. Thiele, W.T. and Dunkel, E., **"Refining Aluminium Silicon Alloys"**, German Patent 1,255,928 (CR.C.22c), December 7th 1967, App. January 13th 1966; 3 pp.

103. Clegg, A.J. and Dos, A.A., **"The Influence of Structural Modifiers on the Refinement of the Primary Silicon in a Hypereutectic Aluminium-Silicon Alloy"**, Br. Foundryman, Vol.71, No. 2, pp 56-63.

104. Brandejs, A., and Holecek, S., **"Long Term Modification of Al-Si Alloys"**, Slevarenstvi, Vol.25, No.3/4, 5th April 1977, pp 100-103.

105. Martin, L.L., and Rodriguez, F.S., **"Permanent Modification of Al-Si Eutectic and near Eutectic Alloys"**. Colada, Vol.10, 1977, pp 221-27 and 249-54.

106. Martin, L.L., and Rodriguez, F.S., **"Modification of Aluminium-Silicon Alloys (of Nearly Eutectic Comp.)"** Fonderie, Vol.32, No.372, pp 353-356.

107. Gobrecht, J., **"The Effect of Additive Elements on the Modification Effect of Sodium and Strontium in Aluminium-Silicon Alloys"**, Giesserei, Vol.65, No.7, 30th March 1978, pp 158-164.

108. Whaler, K., and Griffin, B.J., **"Strontium Modifier Improves Aluminium Casting Quality"**, Mod. Cast., Vol.74, No.8, August 1984, pp 30-31.

109. Vakhobov, A.V., Vasilevskaya, L.E., Ganiev, I.N., and Trubnyakova, E.D., **"Combined Effect of Strontium and Yttrium on the Structure and Properties of AK9 Alloy"**, Liteinoe Proizvod, No.10, October 1982, 32.

110. Patterson, V.H., **"Inoculants for Grey and Spheroidal-Graphite Iron: Their Use and Effect"**, Castings (Sydney), Vol.22, May-June 1976, pp 16-34.

111. Feest, E.A., McHugh, G., Morton, D.O., Welch, L.S., and Cook I.A., **"The Inoculation of Grey Cast Iron"**, Solidification Technology in the Foundry and Casthouse (Proc. Conf.), University of Warwick, Coventry, 15-17 September 1980, The Metals Society, 1981, Paper No. 37.

112. Meyer, L., et al., **"The Production and Properties of a High Strength Pearlitic Titanium Alloy Steel as Hot Strip with Good Forming Properties"**, Thyssen Tech. Ber., Vol.8, No.1, 1976, pp 21-39.

113. Park, B.K., and Shabel, B.S., **"Microstructure and Formability of 6XXX-T4 Alloys"**, Aluminium, Vol.57, No.8, August 1981, pp 527-529.

114. Pacyna, J., and Mazur, A., **"Effect of Grain Size on the Ductility of Tool Steel"**, Wiad. Hutn., Vol.39, No.6, 1983, pp 178-182.

115. Mannan, S.L., Samuel, K.G., and Rodriguez, P., **"Influence of Temperature and Grain Size on the Tensile Ductility of AISI 316 Stainless Steel"**, Mater. Sci. Eng., Vol.68, No.2, January 1985, pp 143-149.

116. Pejcoch, O., **"Methods for Improving the Hot Ductility of High Alloy Chromium Steels"**, Neue Hutte, Vol.21, No.9, September 1976, pp 531-534.

117. Kubachek, V.V., and Sadovskii, V.D., **"Influence of Vanadium on the Recrystallization of Chromium-Molybdenum and Chromium-Nickel-Molybdenum Steels"**, Phys. Met. Metallogr., Vol.43, No.4, 1977, pp 101-107.

118. Norstrom, L.-A., **"The Influence of Nitrogen and Grain Size on Yield Strength in Type AISI 316L Austenite Stainless Steel"**, Material Science, Vol.11, No.6, June 1977, pp 208-212.

119. Ericson, L., **"Cracking in Low Alloy Aluminium Grain Refined Steels"**, Scand. J. Metall., Vol.6, No.3, pp 116-124.

120. Funakoshi, T., et al., **"Improvements in Microstructure and Toughness of Large Heat-Input Weld Bond due to Addition of Rare Earth Metals and Boron in High Strength Steel"**, Tetsu-to-Hagane, Vol.63, No.2, February 1977, pp 303-312.

121. Norstrom, L.-A., **"Influence of Grain Size on Flow Stress in an Austenitic Stainless Steel"**, Scand. J.

Metall., Vol.6, No.4, 1977, pp 145-150.

122. Muschenborn, W., and Meyer, L., **"Cold Rolled Microalloyed Steel Sheets"**, Deep Drawing (Proc. Conf.), Bad Nauheim, 1975, Deutche Gesellschaft fur Metallkunde Ev, Frankfurt/Main, Germany, 1975.

123. Meyers, M.A., and Ashworth, E., **"On the Effect of Grain Size on Yield Stress in Metals. A Theory"**, 36th Annual Congress of ABM (Proc. Conf.), Relife PE, Mexico, 5-10 July 1981, Assoc. Brazileria de Metals, Vol.1, 1981, pp 17-34.

124. Isore, A.J., Abdalla, T.C., and Aleixo, C., **"Influence of Nitrogen, Grain Size and Work Hardening on the Yield Stress of an Austenitic Manganese Steel, DIN 1.3817"**, Metal ABM, Vol.39, No.305, April 1983, pp 193-198.

125. Meyers, M.A., and Ashworth, E., **"A Model for the Effect of Grain Size on the Yield Stress of Metals"**, Philos. Mag. A., Vol.46, No.5, November 1982. pp 737-759.

126. Dollar, M., and Gorczyca, S., **"The Influence of Grain Size on the Work Hardening of an Austenitic Stainless Steel"**, Mater. Sci. Eng., Vol.64, No.2, June 1984, L27-L31.

127. Juva, A., Haavisto, M., **"On the Effects of Microstructure on the Attenuation of Ultrasonic Waves in Austenitic Stainless Steels"**, Annual Assembly 1977, International Inst. of Welding, London, England, 1977.

128. Kubel Jr., E.J., **"Direct Thin Strip Casting"**, Advanced Materials and Processes Inc. Metal Progress, Vol.134, No.9, 1988, pp 55-62.

129. Baer, D.R., and Merz, M.D., **"Differences in Oxides on Large and Small Grained 304 Stainless Steel"**, Metall. Trans. A, Vol.11A, No.12, December 1980, pp 1973-1980.

130. Prater, J.T., Baer, D.R., and Battelle Pacific Northwest Laboratories, **"Improved Corrosion Resistance of Fine Grained 304 Stainless Steel in H_2S-CO-CO_2-N_2 Atmosphere (950°C)"**, DE 83013755, November 1982, 12 pp.

131. Langer, N.A., Slutskaya, T.M., Yushkevich, Z.V., and Gorban, V.A., **"Effect of Carium on the Corrosion Resistance of 09G2D Steel Welded Joints"**, Autom.

Weld. (USSR), Vol.36, No.7, July 1983, pp 44-45.

132. Hasegawa, M., and Osawa, M., **"Corrosion Behaviour of Ultrafine-Grained Austenitic Stainless Steel"**. Corrosion Vol.40, No.7, July 1984, pp 371-374.

133. Leinachuk, E.I., Podgaetskii, V.V., and Parfesso, G.I., **"Effect of Manganese on the Resistance of Weld Metal to the Formation of Solidification Cracks"**, Aurom. Weld., Vol.30, No.12, December 1977, pp 3-5.

134. Batte, A.D., and Murphy, M.C., **"Reheat Cracking in 2.25 Cr-Mo Weld Metal: Influence of Residual Elements and Microstructure"**, Met. Technol., Vol.6, No.2, February 1979, pp 62-68.

135. Kir'yakov, V.M., Kabatskii, V.I., Podgaetskii, V.V. and Parfesso, G.I., **"Effect of Microalloying with Cerium on the Resistance of Austenitic Welds to Cold Cracks in the Fusion Zone"**, Automat. Weld. (USSR), Vol.32, No.10, October 1979, pp 3-6.

136. Metauer, G., Duchanoy, T., and Royer, A., **"Mn-Mo-Nb Weldable Centrifugally Cast Steel Used in the Manufacture of Heavy Wall Pipes for the Offshore Industry"**, Bull. Cercle Etud Metaux, Vol.14, No.15, September 1981, pp 17.1-17.12.

137. Mukae, S., Katoh, M., Nishio, K., and Tashima, K., **"Effects of Titanium and Nitrogen on the Notch Toughness of a Synthetic Weld Heat Affected Zone"**, J. Jpn. Weld. Soc., Vol.51, No.1, January 1982, pp 75 83.

138. Barbazanges, Y., Blanc, G., Baroux, B., and Maitrepierre, Ph., **"Structure and Mechanical Properties of Welds in 17% Cr Stabilized Ferritic Stainless Steels"**, Bull. Cercle Etud Metaux, Vol.14, No.19, September 1982, pp 9.1-9.10.

139. Aziez, B., and Fenn, R., **"Weldability of 18% Cr, 2% Mo Ferritic Stainless Steel Sheet"**, Sheet Met. Ind., Vol.60, No.1, January 1983, pp 28-34.

140. Edwards, R.H., Squires I.F., and Barbaro, F.J., **"The Effect of Titanium Modification on Heat Affected Zone Grain Coarsening Behaviour of Submerged Arc Welds"**, Aust. Weld. J., Vol.31, No.1, Autumn 1986, pp 11-15.

141. Sterenbogen, Yu.A., **"Solidification of the Weld Pool and the Effect of Its Composition on the Chemical Heterogeneity and Susceptibility of Welds to**

Solidification Cracking", Weld Pool Chemistry and Metallurgy (Proc. Conf.) London, England, 15-17 April 1980, Welding Institute, 1980, pp 31-42.

142. Shtinov, E.D., et al., **"Effect of Austenite Grain Size on the Mechanical Properties of Chromium-Nickel Structural Steels"**, Fiz. Khim. O. Mater., Vol.6, November-December 1976, pp 99-.

143. Landgraf, R.W., Sherman, A.M., and Sprys, J.W., **"Fatigue Behaviour of Low Carbon Steels as Influenced by Microstructure"**, Second International Conference on Mechanical Behaviour of Materials (Proc. Conf.), 1976, pp 513-517.

144. Gladman, T., Dulieu, D., and McIvor, I.D., **"Structure/Property Relationships in High Strength Microalloyed Steels"**, Microalloying 75 (Proc.Conf.), Washington DC, October 1975, 1977, pp 32-55.

145. Morosov, M.G., Morosova, I.M., Bonannikov, M.A., and Muller, H.H.. **"Influence of Sulphur on the Properties of Alloyed Steels"**, Neue Hutte, Vol.24, No.5, May 1979, pp 191-192.

146. Thomas, B., Castagne, J.L., Baroux, B., Hebeisen, B., and Maitrepierre, Ph., **"Influence of Metallurgical Parameters on the Mechanical Properties of 13% Cr Martensitic Stainless Steels"**, Bull. Cercle Etud. Metaux, Vol.14, No.9, March 1980, 10 pp.

147. Saito, K., Tajima. K., Yamazaki, K., and Ohta, Y., **"Effect of Nitrogen Content on Low Temperature Properties of Cast Austenitic Stainless Steel, SCS 13"**, Nippon Stainless Tech. Rep., Vol.16, 1981, pp 27-45.

148. Bergstrom, Y., and Hallem, H., **"Hall-Petch Relationships of Iron and Steel"**, Met. Sci., Vol.17, No.7, July 1983, pp 341-347.

149. Fang T.T., and Murty, K.L., **"Grain Size Dependent Creep of Stainless Steel"**, Mater. Sci. Eng., Vol.61, No.3, December 1983, pp L7-L10.

150. Gladman, T., and Pickering, F.B., **"The Effect of Grain Size on the Mechanical Properties of Ferrous Materials (Survey)"**, Yield, Flow and Fracture of Polycrystals (Proc. Conf.) Glasgow, U.K., 15-16 September 1982, Applied Science Publishers, England, 1983, pp 141-198.

Solidification Cracking", Weld Pool Chemistry and Metallurgy (Proc. Conf.) London, England, 15-17 April 1980, Welding Institute, 1980, pp 31-42.

142. Shtinov, E.D., et al., **"Effect of Austenite Grain Size on the Mechanical Properties of Chromium-Nickel Structural Steels"**, Fiz. Khim. Obrab. Mater., Vol.6, November-December 1976, pp 99-103.

143. Landgraf, R.W., Sherman, A.M., and Sprys, J.W., **"Fatigue Behaviour of Low Carbon Steels as Influenced by Microstructure"**, Second International Conference on Mechanical Behaviour of Materials (Proc. Conf.), 1976, pp 513-517.

144. Gladman, T., Dulieu, D and McIvor, I.D., **"Structure/Property Relationships in High Strength Microalloyed Steels"**, Microalloying 75 (Proc.Conf.), Washington DC, October 1975, 1977, pp 32-55.

145. Morosov, M.G., Morosova, I.M., Bolshnikov, M.A., and Muller, H.H., **"Influence of Sulphur on the Properties of Alloyed Steels"**, Neue Hutte, Vol.24, No.5, May 1979, pp 191-192.

146. Thomas, B., Castagne, J.L., Baroux, B., Hebeisen, B., and Maitrepierre, Ph., **"Influence of Metallurgical Parameters on the Mechanical Properties of 13% Cr Martensitic Stainless Steels"**, Bull. Cercle Etud. Metaux, Vol.14, No.9, March 1980, 10 pp.

147. Saito, K., Tajima, K., Yamazaki, K., and Ohta, Y., **"Effect of Nitrogen Content on Low Temperature Properties of Cast Austenitic Stainless Steel, SCS 13"**, Nippon Stainless Tech. Rep., Vol.16, 1981, pp 27-45.

148 Bergstrom, Y., and Hallem, H., **"Hall-Petch Relationships of Iron and Steel"**, Met. Sci., Vol.17, No.7, July 1983, pp 341-347.

149. Fang T.T., and Murty, K.L., **"Grain Size Dependent Creep of Stainless Steel"**, Mater. Sci. Eng., Vol.61, No.3, December 1983, pp L7-L10.

150. Gladman, T., and Pickering, F.B., **"The Effect of Grain Size on the Mechanical Properties of Ferrous Materials (Survey)"** Yield, Flow and Fracture of Polycrystals (Proc. Conf.) Glasgow, U.K., 15-16 September 1982, Applied Science Publishers, England, 1983, pp 141-198.

151. Mannon, S.L., and Rodriguez, P., **"The Influence of Grain Size on Creep Rupture Properties of Type 316 Stainless Steel"**, Advances in Fracture Research (Fracture 84) (Proc. Conf.), New Delhi, India, 4-10 December 1984, Pergamon Press Ltd., U.K., 1984, pp 2303-2309.

152. Welch, P.I., and Bunge, H.J., **"Influence of Grain Size on Plastic Anisotropy in Low Carbon Steels"**, Mater. Sci. Technol., Vol.2, No.4, pp 354-362.

153. Hochstein, F., Austel, W., and Maidorn, Ch., **"Application of a New Processing Procedure for the Further Improvement of Nuclear Grade Structural VCD Steels"**, Nucl. Eng. Des., Vol.81, No.2, September (1) 1984, pp 185-192.

154. Levitin, V.V., Orzhitskaya, L.K., and Kurnavina, L.P., **"The Effect of Alloying with Titanium on the Susceptibility of 40Kh Type Steels to Delayed Fracture During Hydrogen Saturation"**, Izv. Akad. Nauk. SSSR, Met., Vol.6, 1982, pp 136-143.

155. Kanazawa, S., Nakashima, A., Okamato, K., and Kanaya, K., **"Improvement of Weld Fusion Zone Toughness by Fine TiN"**, Trans. Iron and Steel Inst. Jpn., Vol.16, No.9, pp 486-495.

156. Matsuda, S., and Okumura, N., **"Effect of the Dispersion of Titanium Nitride on the Austenite Grain Size in Low Carbon Low Alloy Steels"**, Tetsu-to-Hagane (J. Iron Steel Inst. Jpn.), Vol.62, No.9, August 1976, pp 1209-1219.

157. Jandos, F., Kepka, M., and Kletecka, Z., **"Effect of Metallurgical Factors on the Size of the Primary Grains in Mn-Ni-Cr Austenitic Steels"**, Hutnik (Prague), Vol.25, No.8, August 1975, pp 307-312.

158. Kiselev, L.E., Mikhailov, S.K., Svyatkin, B.K., and Chashnikov, D.I., **"Selection of an Optimum Modifier for (Low Alloy) Steel 12KhN3MFA"**, Liteinoe Proizvod., Vol.10, October 1976, p 5.

159. Lapok, K.B., **"A Study of the Effect of Alloying (Steels) with Niobium"**, Tran. Tu. Trac. IV, Vol.109, No.11, November 1976, pp 494-496.

160. Byun, D.S., Sung, J.H., and Kim, M.I., **"The Effect of Rolling and V, Ti or Zr Addition on the Austenite Grain Size of High Manganese Steels"**, J. Korean Inst. Met., Vol.14, No.1, 1976, pp 52-59.

161. Gavrilin, I.V., Ryzhikov, A.A., Ershov, G.S., and Kalliopin, I.K., **"Choice of Efficient Inoculants for the First Kind of Steel"**, Izv. V.U.Z. Chernaya Metall., Vol.4, 1977, pp 90-94.

162. Bienia, G., **"Modification of Cast Steel"**, Giesserei Technik, Vol 23, No.5, May 1977, pp 136-140.

163. Wood, J.V., **"Nucleation in Steel Castings of Interstitial Compounds"**, Int. Conf. Solidification and Casting, Sheffield, July 1977, (Proc. Conf.), Vol 2, 1977, 12pp.

164. Campbell, J., Caton, P.D., **"The Grain Refinement of Electroslag Remelted Ingots"**, Int. Conf. Solidification and Casting, Sheffield, July 1977, (Supplements), 1977, 28pp.

165. Norring, K., Harvig, H., Lindwall, B., **"Improvements in Thick Plate Steel for Heavy Structures"**, Microalloying 75, Wash. D.C., October 1975, (Proc. Conf.), 1977, pp 684-691.

166. Basarrov, M.F., Bobro, Yu.G., Poryadchenko, P.E., Kazartsev, V.V., and Tsarenck, L.A., **"Increasing the Service Properties of Steel"**, Tekhnol. Organ. Proizvod.Nauchno-Proizvod.Sb., Vol.2, 1977, pp 44-45.

167. Leinachuk, E.I., Podgaetskii, V.V., and Parfesso, G.I., **"Effect of Manganese on the Resistance of Weld Metal to the Formation of Solidification Cracks"**, Autom. Svarka, Vol.10, December 1977, pp 4-6.

168. Kir'yakov, V.M., Kabatskii, V.I., Podgaetskii, V.V., and Parfesso, G.I., **"Effect of Microalloying with Cerium on the Resistance of Austenitic Welds to Cold Cracks in the Fusion Zone"**, Autom. Svarka, Vol.12, 1979, pp 4-7.

169. Bialowas, W., Michaliszn, A., and Fedko, J., **"Effect of Aluminium, Titanium and Boron on the Austenitic Grain Size and Hardenability of Quenched and Tempered Constructional Steels"**, Hutnik (Katowice), Vol.46, No.2, February 1979, pp 71-75.

170. Lanskaya, K.A., and Verevkin, A.N., **"The Effect of Complex Microalloying on the Properties of Chromium-Nickel Austenite Steels"**, Kach. Stali Splavy, (Moskva), Vol.4, 1979, pp 65-68.

171. Mukae, S., Kato, M., and Nishio, K., **"Grain Refining Effect of Ti and Nb in Carbon Steel Welds"**, J. Jpn.

Weld. Soc., Vol.48, No.5, May 1979, pp 266-271.

172. Morosov, M.G., Morosova, I.M., Bonannikov, M.A., and Muller, H.H., **"Influence of Sulphur on the Properties of Alloyed Steels"**, Neue Hutte, Vol.24, No.5., May 1979, pp 191-192.

173. Mukae, S., Katoh, M., and Nihio K., **"Effect of Duplex Addition of Titanium and Nitrogen on Grain Refinement in Weld Heat Affected Zone of Steels"**, J. Jpn. Weld. Soc., Vol.48, No.10, pp 808-813.

174. Itoh, Y., Takao, S. Okajima, T., and Tashiro, K., **"Effects of Alloying Elements and Inoculators on Refining of Solidification Structures of Type 430 Stainless Steel"**, Tetsu-to-Hagane (J. Iron Steel Inst. Jpn.), Vol.66, No.6, May 1980, pp 710-716.

175. Veda, S., Ishikawa, M., and Ohashi, N, **"Enhanced Nucleation of Polygonal Ferrite Grain in the Interior of Austenite Grain in Boron Bearing Steel"**, Boron in Steel (Proc. Conf.), Milwaukee Wis., 18 September 1979, TMS/AIME, 1980, pp 181-198.

176. Markus, E.Ya., Rozin, M.M., and Kats, A.A., **"Inoculation of 55 Kh6V3MFSNL Steel with Cerium"**, Liteinoe Proizvod, Vol.7, July 1980, p 11.

177. Khlinov, V.V., Pastukhov, B.A., Shagalov, V.L., and Furman, E.L., **"Interphase Properties at the Steel-Inclusion Boundary Associated with Structure Refinement"**, Izv. Akad. Nauk. SSSR Met., Vol.5, 1980, pp 39-43.

178. Threadgill, P.L., and Bailey, N., **"The Prospects for Weld Pool Grain Refinement"**, Weld Pool Chemistry and Metallurgy, (Proc. Conf.), London, England, 15-17 April 1980, Welding Institute, 1980, pp 9-16.

179. Thaulow, C., **"Structural Changes in Submerged Arc Weld Metals of CrMn Steels Containing Small Amounts of Titanium"**, ibid, pp 17-29.

180. Bromfin, B.M., Bershtein, L.I., Zhmakina, V.A., and Siper, A.S., **"The Influence of Nitrogen and Aluminium on the Structure and Properties of Cast Low Alloy Steel"**, Izv. V.U.Z. Chernaya Metall., Vol.6, 1980, pp 86-90.

181. Polonskaya, S.M., Piskova, V.P., Chistyakov, V.F., and Averin, V.V., **"Effect of Microalloying and Solidification Conditions on the Ingot Structure and Properties of Steel 20"**, Fiz. Khim. Obrab. Mater.,

Vol.2, 1981, pp 59-66.

182. Monsa, I., **"Effect of Inoculation on Grain Refinement and Mechanical Properties of Cast Steel"**, Przegl. Odlew., Vol.31, No.4, April 1981, pp 117-123.

183. Matrosov, Yu.I., and Sorokon, A.N., **"Improvement in the Mechanical Properties of Low-Pearlite Steels by Microalloying with Vanadium"**, Bynl. NTITsNII Inform Tech.-Ekon. Issled. Chern. Metall., Vol.7, 1981, pp 60-61.

184. Gol'dshtein, M.I., Zhitova, L.P., and Popov, V.V., **"The Influence of Titanium Carbonitrides on the Structure and Properties of Low-Carbon Steels"**, Fiz. Met. Metalloved., Vol.51, No.6, June 1981, pp 1245-1252.

185. Watanabe, I., and Kajima, T., **"Study on the Notch Toughness of Weld Metal in Large Current MIG Arc Welding. II. Role of Titanium and Boron with Respect to the Refinement of the Microstructure"**, J. Jpn. Weld. Soc., Vol.50, No.7, July 1981, pp 702-709.

186. Fiegenschuh, H., **"Effect of Fine Grain Additives on the Grain Size and Mechanical Properties of Transformation Free Austenitic and Ferritic Cast Steel Alloys"**, Thesis, Tech. Univ. Berlin, 1980, 233pp.

187. Fiegenschuh, H., **"Contribution to Grain Refinement of Austenitic and Ferritic Cast Steel Alloys Free of Transformation by Nucleating Additions"**, Giesserei forschung, Vol.33, No.4, 1981, pp 129-138.

188. Axelsson, C.L., and Sjovall, P., **"Addition of Nucleation Agents in ESR Processing of Stainless Steel"**, 2nd Japan-Sweden Joint Symposium on Ferrous Metallurgy, (Preprints Proc. Conf.), Tokyo, Japan, [illegible]ecember 1978, The Iron and Steel Inst. of Japan 1978, pp 180-192.

189. Dehes, P., **"Cast Steels with Fine Grains of Controlled Size. A Response to Economic Requirements and Today's Techniques"** Hommes Fonderie, Vol.122, February 1982, pp 15-21.

190. Bebbington, R.W., Oglesby, J.W., Pearson, J., and London and Scandinavian Metallurgical Co. Ltd., **"Boron Addition to Steel with Improved Recovery"**,

Patent No. GB2086432A (United Kingdom). 7 October 1981.

191. Nagin, A.S., Rybarov, O.K., and Kolakolov, E.I., **"Structure of Cast Stainless Steel Inoculated with Dysprosium"**, Liteinoe Proizvod., Vol.5, May 1982, pp 13-14.

192. Yatsyuk, R.A., **"The Effect of Calcium on the Macrostructure of a 25Yu10S Steel Ingot"**, Fiz. Khim. Mekh. Mater., Vol.5, 1982, pp 113-114.

193. Hurtuk, D.J., and Tzavaras, A.A., **"The Effects of Carbon, Nickel and Phosphorus on the Refinement of Cast Steel Solidification Structures"**, Grain Refinement in Castings and Welds (Proc. Conf.), St. Louis, Mo., U.S.A., 25-26 October 1982, The Metallurgical Society/AIME, 1983, pp 151-163.

194. Banerji, S.K., Staggers, J.O., Lalich, M.J., and Blazek, D.J., **"Strand Cast Boron Steels"**, Electric Furnace Conference Proceedings, 40th (Proc. Conf.), Kansas City, Mo., U.S.A., 7-10 December 1982, Iron and Steel Society/AIME, 1983, pp 329-334.

195. Krucinski, M., and Michaliszyn, A., **"Thermodynamic Analysis of Austenitic Grain Size Coated by Means of Al-Ti-B Alloys"**, Freiberger Forschunhsh. B. Metall. Werkstcfftech., (B239), 1984, pp 97-103.

196. Stuchlik, J., and Spunda, J., **"New Progress in the Development of Wear Resistant Steels and Cast Irons"**, Giesserei-Prax., Vol.11, 12 June 1984, pp 167-176.

197. Heintze, G. [illegible], and McPherson, R., **"Grain Refinement of Steel by Titanium Inoculation During Submerged Arc Welding"**, Aust. Weld. J., Vol.28, No.3, 1983, pp 37-41.

198. Babaskin, Yu.Z., and Shipitsyn, S.Ya., **"The Mechanism of Steel Inoculation"**, Liteinoe Proizvod, Vol.5, May 1984, pp 7-8.

199. Mouchan, M.B., and Efimov, V.A., **"The Mechanism Underlying the Modification of the Primary Structure of Cast Alloys by Disperse Nonmetallic Particles"**, Russ. Metall., Vol.4, 1984, pp 115-121.

200. Zhukov, A.A., Silman, G.I., and Platonov, A.N., **"Certain Characteristics of the Late Inoculation of Steels"**, Russ. Metall., Vol.4, 1984, pp 122-126.

201. Kovalenko, V.S., Kuchkin, V.I., Kisun'ko, V.Z., and Grigorash, A.V., **"Inoculation of Steel by Calcium and Barium"**, Stal' 1985, Vol.7, pp 19-23.

202. Svidunovich, N.A., and Garost, A.I., **"Alloying 110G13L Steel with Nitrogen"**, Liteinoe Proizvod., Vol.5, 1985, pp 12-13.

203. Normann, K.-D., **"Austenitic Manganese Steel of the Hadfield Type, and Process for the Manufacture Thereof"**, B. Kos., 10 April 1985, Patent No. EP0136433 (EUR), 19th July 1984.

204. Yasenko, A.I., Grushko, P.D., Efimenko, E.I., **"The Effect of Cerium on the Crystallization and the Primary Structure of 55S2 Steel"**, Liteinoe Proizvod., Vol.5, 1985, pp 13-14.

205. Michaliszyn, A., Krucinski, M., and Fedko, J., **"Use of Complex FeAlTiB Alloy and the Effects of Austenite Grain Size and Hardenability of Constructional Alloy Steels"**, Arc. Hutn., Vol.30, No.1, 1985, pp 111-124.

206. Staronka, A., and Zajae, M., **"The Influence of Small Calcium and Magnesium Additions on the Structure of Cast Carbon Steel"**, Metal Odlew., Vol.12, No.1, pp 99-105.

207. Lyubchenko, A.P., Kaftanov, S.V., Efimenko, N.G., and Doshchechkina, I.V., **"The Structure and Properties of an Yttrium-Alloyed Cast Carbon Steel"**, Russ. Metall., Vol.5, 1986, pp 104-109.

208. Semen'kov, V.I., Esanlov, V.S., Leonov, I.A., and Sopochkin, A.I., **"Modification of Steel by Rare and Alkaline Earth Metals in the Process of Continuous Casting in an MNLZ Unit"**, Metall. Gornorudn. Prom-st., Vol.3, 1986, pp 14-15.

209. Bordignon, P.J.P., **"Applications of Niobium as a Microalloying Element in Steel"**, SEAISI Q., vol.15, No.2, pp 55-68.

210. Ni, R., Wu, C., Feng S., and Fang, K., **"Function of Cerium in Low Sulfur 16 Mn Steel"**, Iron Steel (China), Vol.21, No.5, 1986, pp 13-19.

211. Bellrose, A., **"Titanium and Boron Additions in the S.A.W. of High Strength Steel"**, Aust. Weld. Res., Vol.14, December 1985, pp 57-63.

212. Gao, R., Chen, H., **"An Investigation of the Improvement of Cast Steel Structure with Rare Earth Elements"**, 1st International Steel Foundry Congress (Proc. Conf.), Chicago, Illinois, U.S.A., 11 - 13 November 1985, Steel Founders' Society of America, 1986, pp 183-192.

213. Bhadeshia, H.K.D.H., Svensson, L.-E., and Gretoft, B., **"A Model for the Development of Microstructure in Low Alloy Steel (Fe-Mn-Si-C) Weld Deposits"**, Acta Metall., Vol.33, No.7, July 1985, pp 1271-1283.

214. Wallace, J.F., **"Changes in Solidified Microstructures"**, Fundamentals of Alloy Solidification Applied to Industrial Processes (Proc. Conf.), Cleveland, Ohio, USA, 12-13 September 1984, National Aeronautics and Space Administration, 1985, pp 91-104.

215. Nakanishi, M., Komizo, Y., and Sefa, I., **"Effect of Titanium Treatment of (Weld Properties of) Low Nitrogen Content Steel"**, Q.J. Jpn. Weld. Soc., Vol.2, No.1, February 1984, pp 33-39.

216. Hochstein, F., Austel, W., and Maidorn, Ch., **"Application of a New Processing Procedure for the Further Improvement of Nuclear Grade Structural VCD Steels"**, Nucl. Eng. Des., Vol.81, No.2, September (1) 1984, pp 185-192.

217. Bialowas, M., Fedko, J., and Michaliszyn, A., **"The Effect of Microalloyed Elements on the Austenitic Grain Size of 40Cr4 Steel Melt"**, Freib. Forschungsh. B., Metall. Werkstofftech., 1982, (B230), pp 87-93.

218. Kovalenko, V.S., and Kuchkin, V **"Dendritic Structure and Inhomogeneity of St Modified with Alkaline Earth Elements"**, Izv. v.U.Z. Chernaya Metall, Vol.8, 1984, pp 103-106.

219. Calenta, E., and Poboril, F., **"Influence of Titanium on Primary Crystallization, Especially in Steels without Alpha-Gamma Transformation"**, Strojnicky Obzor, Vol.15, 1935, pp 511-517. Abstract in Chemical Abstracts, 31 : 1937, p. 6169.

220. Comstock, G.F., **"Titanium in Iron and Steel"**, John Wiley and Sons Inc., 1955.

221. Turnbull, G.K., Patton, D.M., Form G.W., and Wallace, J.F., **"Grain Refinement of Steel Castings and Weld Deposits"**, Trans. of American Foundryman's

Soc., Vol.69, 1961, pp 792-804.

222. Wood, J.V., **"Nucleation in Steel Castings by Interstitial Compounds"** Int. Conf. on Solidification and Casting (Proc. Conf), Sheffield, July 1977, pp 179-183.

223. Hall, H.T., and Jackson, W.J., **"Grain Refinement in Cast Austenitic Steels"**, ISI Pub. 110, 1968, pp 313-317.

224. Jackson, W.J., **"Control of the Grain Structure in Austenitic Steel Castings"**, Iron and Steel, Vol.45, April 1972, pp 163-172.

225. Garland J.G., PhD Thesis, 1972, University of Cambridge; see also Garland J.G., Metal Construction, Vol.6, 1974, p 121.

226. Davies, G.J., and Garland, J.G. **"Solidification Structures and Properties of Fusion Welds"**, Int. Met. Reviews, Vol.20, 1975, pp 83-106.

227. Willingham, D.C., and Bailey, N., **"Chemical Grain Refinament of Submerged Arc Welds"**, Welding Research Int. Vol.7, 1977, pp 28-45.

228. Ostrowski, A., and Langer, E.W., **"The Precipitation of Titanium Carbonitrides in As-Cast 17% Chromium Stainless Steels"**, Scan. J. Metallurgy, Vol.8, 1979, pp 153-160.

229. Collmer, B., and Grinder, O., **"On the Solidification of Low Interstitial Ferritic Chromium Steels"**, Scan. J. of Metall., Vol.9, 1980, pp 151-158.

230. Bellrose, A., **"Titanium and Boron Additions in the S.A.W. of High Strength Steels"**, Australian Welding Research, Vol.14, 1985, pp 57-63.

231. Dowling, J.M., Corbett, J.M., and Kerr, H.W., **"Inclusion Phases and the Nucleation of Acicular Ferrite in Submerged Arc Welds in High Strength Low Alloy Steels"**, Met. Trans. A , Vol.17A, September 1986, pp 1611-1623.

232. Zakharov, M.M., et al., **"Shipbuilding Problems"**, Metallurgica Series, No.21, 1976, pp 62-66 and 67-73.

233. Kiselev, L.E., et al., **"Optimum Additive Selection for Steel 12khN3MFA"**, Russian Castings Production, October 1976, pp 398-399.

234. Povalotskii, D.Ya., et al., **"Influence of Rare-Earth Metals on Structure and Ductility of Chrome-Nickel Stainless Tube Steel"**, Izvest. V.U.Z. Chern. Met., Vol.13, No.10, 1980, pp 108-112.

235. Lippold, J.C., Savage, W.F., **"Solidification of Austenitic Stainless Steel Weldments: Part 2 - The Effect of Alloy Composition on Ferrite Morphology"**, Welding Research Supplement, February 1980, pp 48s-58s.

236. Wieser, P.F., and Wallace, J.F., **"Grain Refinement of Cast Steel by Vacuum Melting"**. AFS Cast Metals Research Journal, March 1966, pp 1-5.

237. Wilson W.G., et al, **"Rare Earth Additions in Continuously Cast Steel"**, Journal of Metals, Vol.37, September 1985, pp 36-41.

238. Waudby, P.E., **"Rare Earth Additions to Steel"**, International Metals Review, No.2, 1978, pp 74-98.

239. Nuri, Y., et al, **"Solidification of Ingots and Continuously Cast Slabs Treated with Rare Earth Metals"**, Trans. I.S.I.J., Vol.22, 1982, pp 399-407.

240. Filippi, P.A., and Vincenzi, G.A., **"Use of Oligoelements in Addition to Aluminium for Refining Austenitic Grains in Structural Alloy Steels"**, 18th National Convention AIM (Proc. Conf.) Verona, Italy, 9-11 Oct. 1978, Assoc. Italiana di Metalurgie, 1978, p 6.

241. Filippi, P.A., and Vicenzi, G.C., **"The Use of Trace Elements in Conjunction with Aluminium for the Control of Austenitic Grain Size in Alloy Structural Steels"**, Metall. Ital., Vol.71, No.1, January 1979, pp 16-21.

242. Ruzicka, D., **"Affecting Austenitic Steel Crystallisation by Fe-Si-Zr Addition"**, Vol.34, No.5, 1986, pp 179-183.

243. Roberts, T.E., Kovarik, D.P., and Maier, R.D., **"The Solidification and Grain Refinement of Cast Austenitic Steels"**, AFS Transactions, Vol.37, 1979, pp 279-298.

244. Heintze, G.N., and McPherson, R., **"Solidification Control of Submerged Arc Welds in Steels by Inoculation with Ti"**, Welding Research Supplement, Vol.65, No.3, 1986, pp 715-825.

245. Emley, E.F., **"Principles of Magnesium Technology"**, Oxford, Pergamon Press, 1966.

246. Cook, I.A., and Feest, E.A., **"Phase Formation and Grain Refinement in the Solidification of Nickel-Aluminium Bronze"**, 1982 Modern Metallography in Metallurgy Conference and Exhibition (Proc. Conf.), Cambridge England, 6-8 September 1982, The Metals Society, England, 1982, Paper 41.

247. Gullman, L.O., and Johansson, L., **"Influence of Composition on Intrinsic Grain Refining in Binary Copper Alloys"**, Solidification and Casting of Metals, (Proc. Conf.), Sheffield, England, July 1977, 1979, pp 198-202.

248. Szkoda, F., and Nitkiewicz, Z., **"Properties of Copper with Boron Microadditives"**, Arch. Hutu., Vol.24, No.4, 1979, pp 559-568.

249. Mannheim, R., Reif, W., **"Grain Refining of Cu-Sn Alloys with Zr, B, and Fe and of Cu-Al Alloys with Ti, B, and Sn"**, The Solidification of Molten Metals (Proc. Conf.) Bad Neuheim, West Germany, 7-8 May 1981, Deutche Gesellschaft fur Metallkunde, W.G., 1982, pp 109-140.

250. Tuttle, B.L., **"Investigations into the Grain Refinement of Copper"**, Pennsylvania State University, Diss. Abstr, Int., Vol.40, No.11, May 1980, p 174.

251. Oya, S., Sayasdhi, M., Toda, Z.. Kombe, H., and Hosaka, K., **"Macrostructural Changes in Cu-Al, Cu-Zn, and Cu-Sn Alloy Castings by the Addition of Pb, Si, Ti and Zr"**, J. Jpn. Copper Brass Res. Ass., Vol. 19, No.19, pp 172-190.

252. Chernov, V.S., **"Influence of Boron and Cerium on Cast Structure of Copper"**, Izvestiya Akademii Nauk SSSR Metally, No.4, 1985, pp 117-121.

253. Elst, R., et al., **"Grain Refinement During Solidification of Cu Based Alloys"**, Z. Metallkde., Vol.77, No.7, 1986, pp 421-424.

254. Weber, G.H., **"Effect of Boron on Castability and Mechanical Properties of Cast Brass Alloys"**, Giesserei, Vol.69, No.3, 1 February 1982, pp 68-72.

255. Galiza, J.A., and Cupini, N.L., **"The Use of Commercial Iron Powder as a Grain Refiner for 70/30**

Brass", 35th Annual Congress of Assoc. Brasileira de Metais (Proc. Conf.) Sao Paulo, Brazil, 6-11 July 1980, Assoc. Brasiliera de Metais, Brasil, 1980, pp 311-324.

256. Ott, D., and Raub, C.J., **"Grain Size of Gold and Gold Alloys: A Review and Some Recent Developments"**, Gold Bull., Vol.14, No.2, April 1981, pp 69-74.

257. Riabkina, M., Gal-Or, L., Fishman, Y., Iram, G., **"Grain Refined Recrystallized 14-Carat Gold Alloy"**, Gold Bulletin, Vol.17, No.2, 1984, pp 62-69.

258. Rapson, W.S., Groenewald, T., **"Gold Usage"**, Academic Press, London, 1978, p 99.

259. Schneider, A., and Hilmer, O., **"Thermal Reduction of Alumina"**, Metall., Vol.14, 1960, pp 186-195.

260. Kurfman, V.B., **"Nucleation Catalysis by Carbon Additions to Magnesium Alloys"**, Trans. AIME, Vol.221, 1961, p 540.

261. Nelson, C.E., **"Grain Size Behaviour in Magnesium Casting Alloys"**, AFS Transactions, 1947, pp 1-23.

262. Hughes, I.C.H., **"Progress in Cast Metals"**, Inst. Metallurgists, London, 1971, p 1.

263. Heubner, U., **"Grain Refinement and Structural Stability of Lead and Lead Alloys by Additions of Sulphur, Selenium and Tellurium"**, Z. Metallkd., Vol.70, No.12, December 1979, pp 761-768.

264. Davies, G.J., **"Solidification and Casting"**, Barking : Applied Science Publishers Ltd., 1973.

265. Chadwick, G.A., **"Heterogeneous Nucleation of Metals from their Melts"**, Metals and Materials, March 1969, pp 77-83.

266. Volmer, M., **"Particle Formation and Particle Action as a Special Case of Heterogeneous Catalysis"**, Z. Electrochem, Vol.35, 1929, pp 555-561.

267. Turnbull, D., **"Kinatics of Heterogeneous Nucleation"**, J. Chem. Phys., Vol.18, 1950, pp 198-203.

268. Funk, E.R., and Udin, H., **"Brazing Hydromechanics"**, Welding J., Vol.31, 1952, pp 310s-316s.

269. Volmer, M., and Weber, A., **"Nucleus Formation in Supersaturated Systems"** Z. Phys. Chem., Vol.119, 1926, pp 227-301.

270. Becker, R., and Doring, W., **"The Kinetic Treatment of Nuclei Formation in Supersaturated Vapors"**, Ann. Phys., Vol.24, 1935, p 719.

271. Sundquist, B.E. and Mondolfo, L.F., **"Orientation Relations in the Heterogeneous Nucleation of Solid Lead from Liquid Lead"**, Trans. TMS-AIME, Vol.221, 1961, pp 607-613.

272. Pound, G.M., **"Liquid Metals and Solidification"**, ASM, 1958, p 87.

273. Tiller, W.A., and Takahashi, T., **"The Electrostatic Contribution in Heterogeneous Nucleation Theory: Pure Liquids"**, Acta Metallurgica, Vol.17, April 1969, pp 483-496.

274. Turnbull, D., and Vonnegut, R., **"Nucleation Catalysis"**, Ind. Eng. Chem., Vol.44, 1952, pp 1292-1298.

275. Bradshaw, F.J., Gasper, M.E., and Pearson, S., **"The Supercooling of Gold as Affected by Some Catalysts, Part I"**, J. Inst. Metals, Vol.87, 1958, pp 15-18.

276. Sundquist, B.E., and Mondolfo, L.F., **"Heterogeneous Nucleation in the Liquid to Solid Transformation of Alloys"**, Trans. TMS-AIME, Vol.221, 1961, pp 157-164.

277. Reynolds, J.A., and Tottle, C.R., **"The Nucleation of Cast Metals at the Mold Face"**, J. Inst. of Metals, Vol.80, 1951, Paper No. 1328, pp 93-98.

278. Glicksman, M.E., and Childs, W.J., **"Nucleation Catalysis in Supercooled Liquid Tin"**, Acta Met., Vol.10, 1962, pp 925-933.

279. Turnbull, G.K., Patton, D.M., Form, G.W., and Wallace, J.F., **"Grain Refinement of Steel Castings and Weld Deposits"**, Trans. Am. Foundrymen's Society, Vol.69, 1961, pp 792-804.

280. Wallace, J.F., **"Grain Refinement of Steels"**, Proc. Electric Furnace Conf., 1962, pp 125-139.

281. Turnbull, G.K., Form, G.W., and Wallace, J.F., **"Development of As-Cast Grain Refiner for Cast Steel"**, US Dept. Com., Office Tech. Serv., AD 258,793, 1960, 63pp, US Patent No. 3,308,515.

282. Wallace, J.F., **"Grain Refinement of Steels"**, J. Metals, Vol.15, 1963, p 372.

283. Crosley, P.B., Douglas, A.W., and Mondolfo, L.F., **"Interfacial Energies in Heterogeneous Nucleation"**, ISI Pub. 110, 1967, pp 10-17.

284. Bramfitt, B.L., **"The Effect of Carbide and Nitric Additions on the Heterogeneous Nucleation Behaviour of Liquid Iron"**, Metallurgical Transactions, Vol.1, July 1970, pp 1987-1995.

285. Rutter, J.W., and Chalmers, B., **"Prismatic Substructure Formed During Solidification of Metals"**, Can. J. Phys., Vol.31, 1953, pp 15-39.

286. Chalmers, B., **"Principles of Solidification"**, John Wiley and Sons Inc., New York 1964.

287. Walton, D. and Chalmers, B., **"The Origin of the Preferred Orientation in the Columnar Zone of Ingots"**, Transactions of the Metallurgical Society of AIME, vol.215, June 1959, pp. 447-456.

288. Hellawell, A. and Herbert, P.M., **"The Development of Preferred Orientations during the Freezing of Metals and Alloys"**, Proc. of the Royal Society, vol. A 269, 1962, pp. 560-573.

289. Winegard, W.C. and Chalmers, B., **"Supercooling and Dendritic Freezing in Alloys"**, Transactions of the American Soc. for Metals, vol. 46, 1954, pp. 1214-1224.

290. Tiller, W.A., Jackson, K.A., Rutter, J.W., and Chalmers, B., **"The Redistribution of Solute Atoms During the Solidification of Metals"**, Acta Met., Vol.1, 1953, pp 428-437.

291. Flemings, M.C., **"Solidification Processing"**, New York, McGraw Hill, 1974

292. Beeley, P.R., **"Foundry Technology"**, Butterford Scientific, London, 4th Ed., 1982

293. Winegard, W.C., **"Fundamentals of the Solidification of Metals"**, Metallurgical Reviews, vol. 6, 1961, pp. 57-99

294. Tarshis, L.A., Walker, J.L., and Rutter, J.W., **"Experiments on the Solidification Structure of Alloy Castings"**, Metallurgical Transactions, Vol.2, September 1971, pp 2589-2597.

295. Ostrowski, A., and Langer, E.W., **"Influence of Alloying Elements on the As-cast Structure of 17% Chromium Stainless Steels"**, Scand. J. Metallurgy, Vol.8, 1979, pp 117-184.

296. Youdelis, W.V., **"Nucleation Entropy and Supercooling in Alloys"**, Metal Science, Vol.9, 1975, pp 464-466.

297. Youdelis, W.V., **"Nucleation Entropy and Grain Refinement of Alloys"**, Metal Science, Vol.13, 1979, pp 540-543.

298. Youdelis, W.V., **"Calculated Al-Ti-Si Phase Diagram and Interpretation of Grain Refinement Results"**, Metal Science, Vol.12, 1978, pp 363-366.

299. Youdelis, W.V., Yang, C.S., **"$Ti_5(Al, Si)_3$ Compound Formation in Non-Equilibrated Al-Ti-Si Alloy"**, Metal Science, Vol.14, 1980, pp 500-501.

300. Youdelis, W.V., Yang, C.S., **"Beryllium-Enhanced Grain Refinement of Aluminium-Titanium Alloys"**, Metal Science, Vol.16, 1982, pp 275-281.

301. Youdelis, W.V., Kwon, O., **"Carbide Phases in Cobalt Base Superalloy: Role of Nucleation Entropy in Refinement"**, Metal Science, Vol.17, 1983, pp 379-384.

302. Youdelis, W.V., Kwon, O., **"Carbide Phases in Nickel Base Superalloy: Nucleation Properties of MC Type Carbide"**, Metal Science, Vol.17, 1983, pp 385-388.

303. Petersen, W.A., **"Fine Grained Weld Structures"**, Welding Research Supplement, Vol.52, February 1973, pp 74s-79s.

304. Suzuki, A., Nakaoka, Y., **"Dendrite Morphology and Arm Spacing of Steels"**, J. Jpn. Inst. Met., Vol.33, 1969, pp.658-663.

305. Gurashov, V.N., Korov, I.E., Barbashin, O.A., Samoilovid, S.S., **"Alloying of Steel Kh18N22V2T2 with Rare Earth Metals"**, Metalloved nie i Termicheskaya Obrabotka Metallov, No.8, August 1971, pp.73-75.

306. Rivlin, V.G. and Raynor, G.V., **"Critical Evaluation of Constitution of Chromium-Iron-Nickel System"**, International Metals Review, Vol.25, no.1, 1980, pp.21-38.

307. **"A Guide to the Solidification of Steels"**, Jernkontoret, Stockholm, 1977.

308. Fredriksson, H., **"The Solidification Sequence in an 18-8 Stainless Steel, Investigated by Directional Solidification"**, Metallurgical Transactions, Vol.3, November 1972, pp. 2989-2997.

309. Wolf, M., **"Strand Surface Quality of Austenitic Stainless Steels: Part 2 Microscopic Solidification Structure"**, Iron Making and Steel Making, Vol.13, no.5, 1986, pp.258-262.

310. Hultgren, A., **"Crystallization and Segregation Phenomena in 1.10% Carbon Steel Ingots of Smaller Sizes"**, Journal of Iron and Steel Institute, Vol.70, 1929, pp.69-113.

311. Apelian, D., Ozgu, M.R., **"Direct Casting of Thin Steel Sections-A Tutorial Review"**, Modelling of Casting and Welding Processes IV, Edited by A.F. Gimaei and G.J. Abbaschian, The Minerals, Metals and Materials Society, U A, 1988.

312. Tiller, W.A., **"Grain Size Control During Ingot Solidification"**, Journal of Metals, Vol.11, no.8, 1959, p. 512.

313. Rappaz M., **"Modelling of Microstructure Formation in Solidification Processes"**, International Materials Reviews, Vol.34, no.3, 1989, pp. 93-123.

314. Okamoto, T., Kishitake, K., **"Dendritic Structure in Unidirectionally Solidified Aluminium, Tin, and Zinc Base Binary Alloys"**, J. Crystal Growth, Vol. 29, 1975, pp. 137-146

315. Kurz, W., Trivedi, R., **"Solidification Microstructures: Recent Developments and Future Directions"**, Acta Metall. Mater., Vol.38, no.1, 1990, pp.1-17

316. Church, N.L., **"Nucleation and Constitutional Supercooling Effects on Cast Steel Properties"**, PhD Thesis, Case Institute of Technology, 1965.

317. Gautschi, R.H., Langenberg, F.C., **"Effect of Rare Earth Additions on Some Stainless Steel Melting Variables"**, Transactions of the Metallurgical Society AIME, Vol.218, no. 2, 1960, pp. 128-132.

318. Flemings, M.C., Barone, R.V., Uran, S.Z. and Taylor, H.F., **"Solidification of Steel Castings and Ingots"**, Trans. AFS, Vol.69, 1961, pp. 422-435.

319. Church, N., Wieser, P., Wallace, J.F., **"Control of Cast Grain Size of Steel Castings, Effect of Grain Refinement on Properties"**, U.S. Army Materials Research Agency, Watertown, Massachusetts, Technical Report AMRA-CR 64-04/2.

Author: Ozbayraktar Serdar.

Name of thesis: Modification of the cast structure of stainless steel AISI310s and its influence on mechanical properties.

PUBLISHER:

University of the Witwatersrand, Johannesburg
©2015

LEGALNOTICES:

Copyright Notice: All materials on the University of the Witwatersrand, Johannesburg Library website are protected by South African copyright law and may not be distributed, transmitted, displayed or otherwise published in any format, without the prior written permission of the copyright owner.

Disclaimer and Terms of Use: Provided that you maintain all copyright and other notices contained therein, you may download material (one machine readable copy and one print copy per page)for your personal and/or educational non-commercial use only.

The University of the Witwatersrand, Johannesburg, is not responsible for any errors or omissions and excludes any and all liability for any errors in or omissions from the information on the Library website.