

BaMn₂P₂: Highest magnetic ordering temperature 122-pnictide compoundB. S. Jacobs^{1,*} and Abhishek Pandey^{2,3,†}¹*Department of Physics, University of Johannesburg, Johannesburg 2006, Gauteng, South Africa*²*Materials Physics Research Institute, School of Physics, University of the Witwatersrand, Johannesburg 2000, Gauteng, South Africa*³*Department of Physics and Astronomy, Texas A&M University, College Station, Texas 77843, USA*

(Received 22 February 2023; accepted 7 April 2023; published 21 April 2023)

We report the growth of high-quality single crystals of ThCr₂Si₂-type tetragonal BaMn₂P₂ and investigation of its structural, electrical transport, thermal, and magnetic properties. Our results of basal plane electrical resistivity and heat capacity measurements show that the compound has an insulating ground state with a small band gap. Anisotropic susceptibility $\chi_{ab,c}(T)$ data infer a collinear local-moment Néel-type antiferromagnetic (AFM) ground state below the ordering temperature $T_N = 795(15)$ K, which is highest among all the ThCr₂Si₂- and CaAl₂Si₂-type 122-pnictide compounds reported so far suggesting that the strength of magnetic exchange interactions is strongest in this material. The magnetic transition temperatures of BaMn₂Pn₂ ($Pn = P, As, Sb, Bi$) compounds exhibit a monotonic decrease with the increase of tetragonal unit cell parameters a and c , suggesting a strong dependence of the strength of the decisive magnetic exchange interactions on the separation between the localized spins residing on the Mn ions. The observed monotonic increase of both χ_{ab} and χ_c for $T > T_N$ suggests that short-range dynamic quasi-two-dimensional AFM correlations persist above the T_N up to the highest temperature of the measurements. The large T_N of BaMn₂P₂ demands for systematic hole-doping studies on this material as similar investigations on related BaMn₂As₂ with $T_N = 618$ K have led to the discovery of an outstanding ground state where AFM of localized Mn spins and itinerant half-metallic ferromagnetism with $T_c \approx 100$ K originating from the doped holes coexist together.

DOI: [10.1103/PhysRevMaterials.7.044410](https://doi.org/10.1103/PhysRevMaterials.7.044410)**I. INTRODUCTION**

The search for new transition metals-based superconductors and their probable parent compounds got intensified after the discovery of high-temperature (high- T_c) superconductivity (SC) in iron-based layered pnictides and chalcogenides [1–5]. Specifically, after the discovery of SC in doped-BaFe₂As₂, significant efforts were put into the investigations of ThCr₂Si₂-type 122-tetragonal systems that crystallize with space group $I4/mmm$. The investigations carried out so far suggest that iron is an essential ingredient for achieving high- T_c SC within this family of compounds. On the other hand, exploratory efforts on related systems where in place of iron some other 3d or 4d transition metal ions constitute the metal-pnictide sublattice have led to quite interesting outcomes and ground states such as prototypical half-metallic behavior [6–8], spin-liquid phase embedded with antiferromagnetic (AFM) and ferromagnetic (FM) fluctuations [9–11], highly frustrated itinerant magnetism [12], low-temperature SC [13–16], discovery of new layered magnetic phases [17], large negative magnetoresistance (MR), and Anderson localization [18–20], to name a few.

Among the 122-type materials, Mn-based AMn₂Pn₂ ($A = Ca, Sr, Ba$, and $Pn = P, As, Sb, Bi$) semiconducting compounds have received special attention. Irrespective of the

type of pnictide ion present, the Ca- and Sr-based AMn₂Pn₂ materials crystallize in CaAl₂Si₂-type trigonal structure with space group $P\bar{3}m1$ while the Ba-based compounds crystallize in ThCr₂Si₂-type tetragonal structure, suggesting that alkaline earth metals are the controlling factor for establishment of the ground-state crystal structure in these systems. Further, pnictide atoms control the unit-cell dimensions, hence, the separation between magnetic Mn ions [21,22]. As a result, with two accessible composition-based tunable control parameters, these systems offer immense opportunities for the investigation of structure-interactions-property relationship.

Specifically, small band gap semiconducting BaMn₂Pn₂ compounds with stacked-square-lattice of Mn ions undergo G-type AFM ordering with Néel temperature T_N considerably higher than room temperature (Table I). Interestingly, the most well-studied member of this family, BaMn₂As₂, undergoes insulator-to-metal transition by a small amount (<2%) of hole-doping [23] or by the application of moderate ~ 6 GPa pressure [24]. Unlike the related itinerant AFM spin-density wave compound BaFe₂As₂, where hole-doping leads to the formation of SC ground state [3–5], the higher levels of hole-doping ($\gtrsim 40\%$) results in stimulating prototype half-metallic behavior in BaMn₂As₂ [6–8].

In contrast to the thoroughly investigated As-, Sb-, and Bi-based counterparts [25–28], limited amount of experimental work has been reported on BaMn₂P₂. About two decades ago, Brock *et al.* performed magnetic susceptibility and neutron diffraction studies on a polycrystalline sample of BaMn₂P₂ and suggested that the material is a high-spin G-type

*sjacobs@uj.ac.za

†abhishek.pandey@wits.ac.za

TABLE I. Structural and physical properties parameters of BaMn_2Pn_2 ($Pn = \text{P, As, Sb, Bi}$). All four compounds crystallize in ThCr_2Si_2 -type tetragonal structure with space group $I4/mmm$ (SG: 221). The listed crystallographic parameters are the unit cell parameters a , c , c/a , z_{Pn} , and the distance between two nearest interlayer pnictogen atoms d_{Pn-Pn} . The listed physical properties parameters are Néel temperature T_N , Sommerfeld coefficient γ , coefficient β and δ of lattice heat capacity, Debye temperature Θ_D , and band gap Δ obtained from the resistivity measurements.

Parameter	BaMn_2P_2 (This paper)	BaMn_2As_2 Ref. [25]	BaMn_2Sb_2 Ref. [26]	BaMn_2Bi_2 Ref. [27]
Structure parameters				
a (Å)	4.0381(1)	4.1686(4)	4.397(4)	4.4902(3)
c (Å)	13.0653(3)	13.473(3)	14.33(2)	14.687(1)
c/a	3.2355(2)	3.232(1)	3.259(8)	3.2709(5)
z_{Pn}	0.3568(2)	0.3615(3)	0.3642(1)	0.3692(3)
d_{Pn-Pn} (Å)	3.742(5)	3.732(9)	3.89(1)	3.84(1)
Property parameters				
T_N (K)	795(15)	618(3)	450(10)	387.2(4)
γ (mJ/mol K ²)	0.9(9)	0.0(4)	0.02(4)	0
β (mJ/mol K ⁴)	0.23(3)	0.65(3)	0.680(3)	0.434(3)
δ (mJ/mol K ⁶)	0.0027(1)	0	0	0
Θ_D (K)	348(17)	246(4)	202(1)	165
Δ (meV)	24(2)	27 & 6.5	160 and 18	

antiferromagnet where Mn spins carry a moment of 4.2(1) μ_B and $T_N > 750$ K [29,30]. After their work, there was no further attempt to investigate the properties of this material. In this paper we report the single crystal growth as well as structural, electronic, magnetic, and thermal properties of BaMn_2P_2 and attempt to establish structure-property relationship within insulating BaMn_2Pn_2 compounds. We show that the value of T_N in BaMn_2P_2 is highest among the 122-pnictide compounds. Additionally, our results also establish a strong correlation of the value of T_N on intralayer as well as interlayer distance between the Mn ions.

II. EXPERIMENTAL DETAILS

Single crystals of BaMn_2P_2 were grown using solution growth technique in Sn flux using high purity starting elements Ba (99.99%), Mn (99.98%), P (99.999%), and Sn (99.999%) weighed in the molar ratio Ba:Mn:P:Sn = 1:2:2:45. The required amounts of the pure elements were placed in an alumina crucible and sealed inside a quartz tube under a partial Ar pressure of about 0.25 atm. The sealed tube was placed in a furnace and heated from room temperature to 400 °C in 10 h and held at this temperature for 30 h. The assembly was further heated to 1180 °C in 25 h and maintained at this temperature for 40 h. Further, it was slow-cooled to 700 °C in 130 h. At this temperature, the Sn flux was decanted [31] using a centrifuge and shiny plate-like crystals of BaMn_2P_2 of typical size of $2 \times 2 \times 0.5$ mm³ were obtained. Room temperature powder x-ray diffraction (XRD) measurement was performed on a few small crushed crystals of BaMn_2P_2 using a Bruker D8 Advance Powder Diffractometer equipped with a Cu-K α radiation source. Two-phase Rietveld refinement was performed using the FullPROF package [32].

Temperature T dependence of heat capacity C_p as well as four-probe basal ab -plane electrical resistivity ρ_{ab} measurements were done using a Physical Properties Measurement System (PPMS) of Quantum Design Inc. (QDI), USA. Single component silver-filled epoxy was used for making electrical contacts of platinum wires on the single crystal for electrical measurements. Temperature dependence of anisotropic magnetic susceptibilities $\chi_{ab,c}(T)$ were measured using two different options: for $2 \text{ K} \leq T \leq 400 \text{ K}$ using a SQUID-Magnetic Properties Measurement System (MPMS) of QDI and for $350 \text{ K} \leq T \leq 850 \text{ K}$ using the high-temperature Vibrating Sample Magnetometer (VSM) Option of a PPMS. Isothermal magnetization M versus applied field H at five different temperatures were measured using MPMS.

III. RESULTS

A. Crystal structure

The powder XRD data collected on a few crushed crystals of BaMn_2P_2 along with the two-phase Rietveld refinement fit, difference profile and Bragg positions are shown in Fig. 1. The two-phase Rietveld refinement was performed to include the reflections originating from the small amount of adventitious Sn flux remaining on the surface of the small crystals that were crushed to powder. The fitted values of the tetragonal lattice parameters a , c , and the c -axis phosphorus position parameter z_P of BaMn_2P_2 are listed in Table I along with the corresponding parameters of BaMn_2As_2 , BaMn_2Sb_2 , and BaMn_2Bi_2 . Figures 2(a) and 2(b) show the variation of the lattice parameters a and c , respectively, of the four BaMn_2Pn_2 compounds with the type of pnictogen atom present in the unit cell. The results highlight a nearly linear increase in a and c as we go down in the group from P to Bi. Due to the linear variation in the lattice parameters, the c/a ratio of these materials

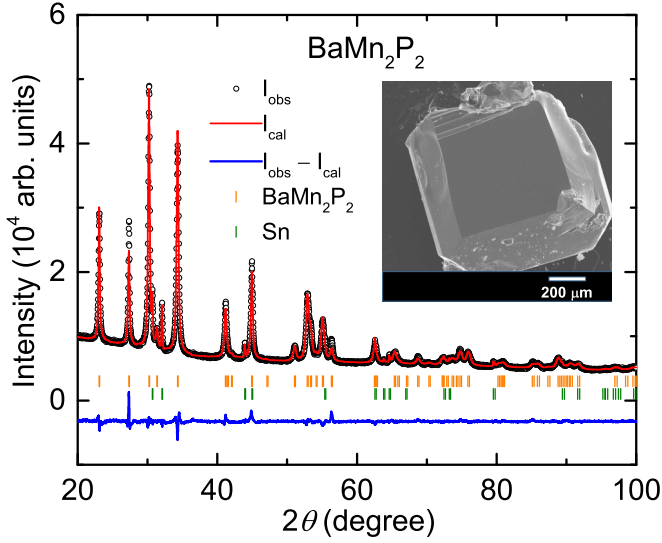


FIG. 1. Room temperature powder x-ray diffraction data collected on Sn-grown crushed crystals of BaMn₂P₂, two-phase Rietveld refinement profile, difference profile, and Bragg positions of BaMn₂P₂ as well as adventitious Sn. Inset: Scanning electron microscope image of a crystal of BaMn₂P₂.

stay nearly constant at a value of 3.25(2) (Table I). In contrast to the large variation of the a and c parameters, the distance between adjacent pnictogen layers $d_{Pn-Pn} = c(1 - 2z_{Pn})$ does not show any noteworthy dependence on the type of pnictogen present in the lattice and exhibits a nonmonotonic behavior with a mean value of 3.81(8) Å [Fig. 2(c)]. It is also important to highlight here that the intralayer distances between nearest (NN)- and next-nearest-neighbor (NNN) Mn spins are $a/\sqrt{2}$ and a , respectively, while the interlayer distance between the two adjacent Mn spins along the c axis is $c/2$.

B. Electrical transport

Figure 3 shows the ab -plane electrical resistivity ρ_{ab} of a single crystal of BaMn₂P₂ versus T for two different applied fields $\mu_0 H = 0$ and 7 T. The $\rho_{ab}(T)$ stays nearly constant and exhibits a small increase of about 10% with decreasing T from 300 K to ~ 130 K [inset (a), Fig. 3]. However, there

is a sharp rise in the $\rho_{ab}(T)$ values below 130 K where it shows a fourfold increase and becomes nonmeasurable with the PPMS electronics below ~ 70 K. This observation clearly suggests that similar to the As-, Sb-, and Bi-based analogs BaMn₂P₂ has an insulating ground state. Additionally, $\rho_{ab}(T)$ data collected at $\mu_0 H = 0$ and 7 T overlap with each other in the entire T range of measurement. This observation suggests that $\mu_0 H \leq 7$ T does not have any measurable effect on the interactions and scatterings that dominate the electrical transport within the ab plane of this compound, leading to negligible magnetoresistance. The $\rho_{ab}(T)$ data below $\lesssim 100$ K show feature of activated transport [inset(b), Fig. 3] and were fitted using

$$\ln \rho_{ab}(T) = A + \frac{\Delta}{k_B T}, \quad (1)$$

where A is a constant, Δ is activation energy of the band gap, and k_B is Boltzmann constant. The fitted value of $\Delta = 24(2)$ meV suggests it to be a small band gap material. This value is similar to the values reported on a polycrystalline sample of BaMn₂P₂ [30] as well as single crystals of BaMn₂As₂ and BaMn₂Sb₂ (Table I).

C. Heat capacity

The heat capacity at constant pressure C_p versus T data of BaMn₂P₂ do not show evidence of any phase transition below room temperature and attain a value of 122.7 J/mol K² at 291 K (Fig. 4). This value is close to the Dulong-Petit high- T limit of lattice heat capacity at constant volume given by $C_V = 3nR = 15R = 124.7$ J/mol K², where $n = 5$ is the number of atoms per unit cell and R is the gas constant. Attempt to fit the $C_p(T)$ data using Debye model of acoustic phonons [33,34] led to a poor agreement especially at intermediate temperatures. This observation is not surprising as Debye model works well both at low temperatures ($T \ll \Theta_D$) where it predicts a T^3 dependence of C_V and at high temperatures ($T \gtrsim \Theta_D$) where it leads to the Dulong-Petit limit. Here Θ_D is Debye temperature of the material under consideration. However, the model often becomes inconsistent with the experimental results at intermediate temperatures. Often for materials with high Θ_D , one gets a significantly improved fit by incorporating a weighted Einstein single-frequency con-

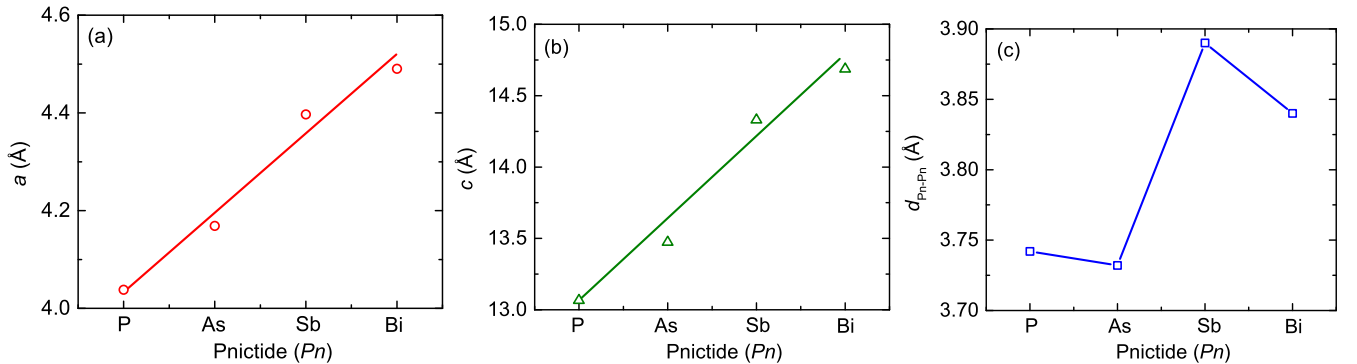


FIG. 2. Variation of tetragonal lattice parameters (a) a , (b) c , and (c) the distance between adjacent pnictogen layers d_{Pn-Pn} in BaMn₂Pn₂ ($Pn = P, As, Sb, Bi$) with the type of pnictide ion present in the unit cell.

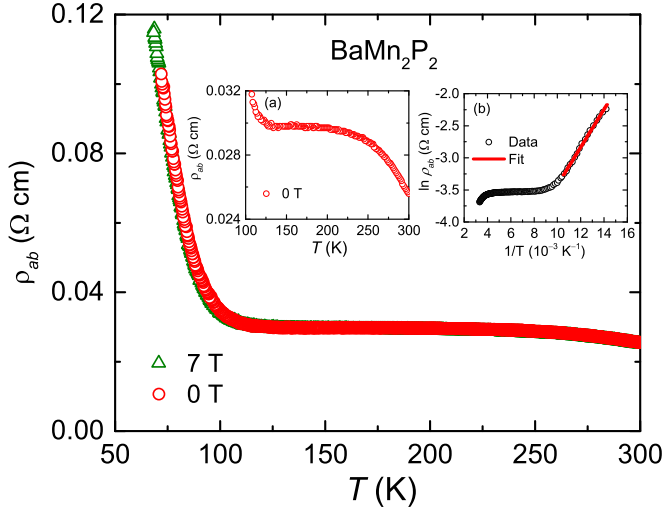


FIG. 3. Electrical resistivity ρ_{ab} vs temperature T of BaMn_2P_2 measured at two different applied magnetic fields $\mu_0 H = 0$ and 7 T. Insets (a) $\rho_{ab}(T)$ for $100 \leq T \leq 300$ K and (b) $\ln \rho_{ab}$ vs T^{-1} along with a linear fit performed for $2 \text{ K} \leq T \leq 95 \text{ K}$.

tribution to the Debye model as in

$$C_p(T) = u C_{V\text{Debye}}(T) + (1 - u) C_{V\text{Einstein}}(T), \quad (2)$$

where $C_{V\text{Debye}}(T)$ and $C_{V\text{Einstein}}(T)$ are the Debye and Einstein contributions, respectively, and u is fraction of the Debye contribution to the lattice heat capacity [34]. We got a good agreement to the $C_p(T)$ data using Eq. (2) and the fitted value of u , Θ_D , and Einstein temperature Θ_E were 0.324(6), 498(4), and 118(1) K, respectively. As expected, the fitted value of the Θ_D is higher than room temperature.

The low-temperature $C_p(T)$ data were fitted using

$$C_p/T = \gamma + \beta T^2 + \delta T^4, \quad (3)$$

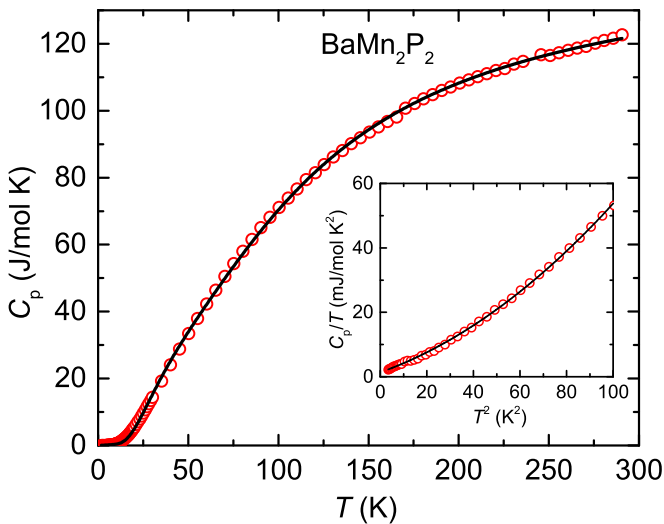


FIG. 4. Heat capacity C_p vs temperature T along with the Debye-Einstein fit as described in the text. Inset: C_p/T vs T^2 data for $T \leq 10 \text{ K}$ along with the fit as described in the text.

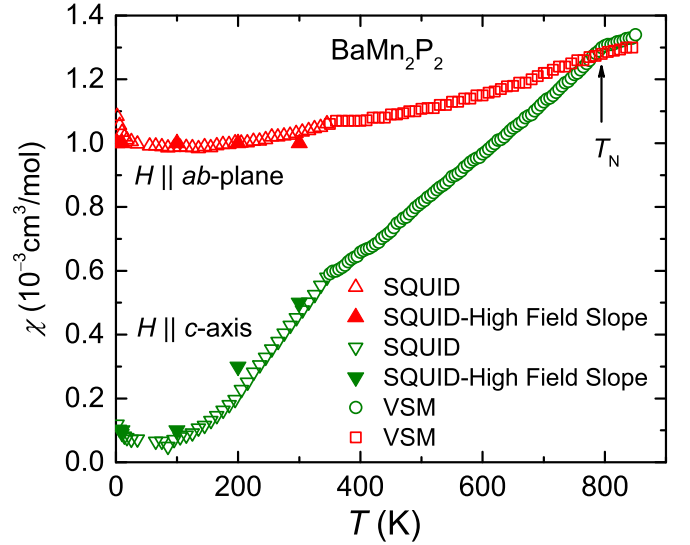


FIG. 5. Anisotropic magnetic susceptibilities $\chi_{ab,c} \equiv M/H$ vs temperature T of BaMn_2P_2 measured using a SQUID-magnetometer at $\mu_0 H = 3 \text{ T}$ for $T \leq 350 \text{ K}$, determined from high-field slopes of the isothermal magnetization measurements and measured using a vibrating sample magnetometer for $T \geq 350 \text{ K}$.

where γ is the Sommerfeld electronic heat capacity coefficient while β and δ are the coefficients of low temperature lattice contributions. We obtained a good fit to the low-temperature $C_p(T)$ data using Eq. 3 [inset, Fig. 4] and the fitted values of the parameters are; $\gamma = 0.9(9) \text{ mJ/mol K}^2$, $\beta = 0.23(3) \text{ mJ/mol K}^4$, and $\delta = 0.0027(1) \text{ mJ/mol K}^6$. As expected for a material with insulating ground state, the γ is nearly zero indicating absence of density of states at Fermi level E_F at low temperatures. The low- T Θ_D calculated from the value of β using $\Theta_D = (12\pi^4 R n / 5\beta)^{1/3} = 348(17) \text{ K}$ is significantly higher than those reported for As-, Sb-, and Bi-counterparts (Table I).

D. Magnetism

Temperature dependence of the magnetic susceptibilities χ_{ab} ($H \parallel ab$ plane) and χ_c ($H \parallel c$ axis) of a crystal of BaMn_2P_2 measured at $\mu_0 H = 3 \text{ T}$ are shown in Fig. 5. The $\chi(T)$ data taken using a SQUID magnetometer for $T \leq 400 \text{ K}$ and those collected using a PPMS-VSM for $T \geq 350 \text{ K}$ connect nearly smoothly, leaving a minor kink at 350 K that likely arises due to slight variation in the orientations of the crystal relative to H when mounted on two different set-ups. The SQUID data are shown up to 350 K for clarity of the figure. The observed T dependence of the anisotropic $\chi_{ab,c}$ data suggests that similar to the As-, Sb-, and Bi-based analog compounds, BaMn_2P_2 has a collinear AFM ordering where the localized spins are oriented along the c axis of the tetragonal unit cell. The $T_N = 795(15) \text{ K}$ deduced from the $\chi_{ab,c}(T)$ data is considerably higher than that observed in the other three materials, suggesting the presence of comparatively stronger magnetic interactions in BaMn_2P_2 . Further, the $\chi_{ab,c}(T)$ data show a monotonic increase above T_N suggesting the persistence of dynamic short-range quasi-two-dimensional AFM corre-

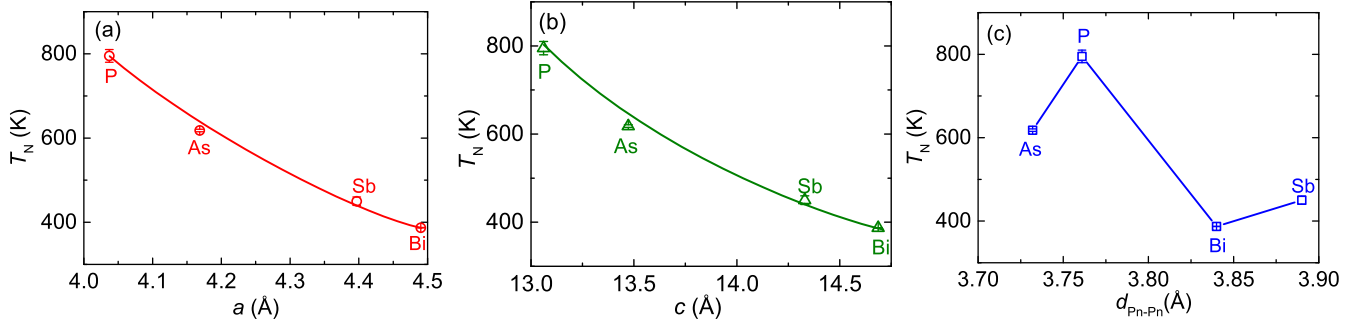


FIG. 6. Variation of antiferromagnetic transition temperature T_N with tetragonal unit cell parameters (a) a , (b) c , and (c) distance between adjacent pnictogen layers d_{Pn-Pn} in BaMn₂Pn₂ ($Pn = P, As, Sb, Bi$).

lations above the ordering temperature, a behavior, which was earlier observed in the other three compounds discussed above. The results show that T_N of BaMn₂Pn₂ ($Pn = P, As, Sb, Bi$) exhibits a monotonic decrease with increase in the tetragonal unit cell parameters a and c [Figs. 6(a) and 6(b)]. This observation infers the progressive weakening of the magnetic interactions operating between the localized Mn spins with increase of the separation between them. While moving from BaMn₂P₂ to BaMn₂Bi₂ we observe nearly 50% reduction in T_N by approximately 12% increase in the a and c (Table I). Our observations also clearly demonstrate that the T_N values do not have any direct correlation with the d_{Pn-Pn} in these materials [Fig. 6(c)].

Isothermal magnetization M of a single crystal of BaMn₂P₂ versus applied magnetic field H for two orientations of the applied field $H \parallel ab$ plane and $H \parallel c$ axis are shown in Figs. 7(a) and 7(b), respectively. As expected for a local-moment AFM system below its ordering temperature, the M is proportional to H for both orientations of the applied field for $T \leq 300$ K. The slight nonlinearity in the $M_{ab}(H)$ data at 2 K indicates the presence a very small amount of saturable paramagnetic or FM impurities in the crystal. The

same was inferred by the small upturn observed in the $\chi_{ab}(T)$ below ~ 10 K (Fig. 5). Evidently the effect of these impurities is almost negligible in the T range of our measurements. However, we still attempted to get the intrinsic susceptibilities at low temperatures from the high-field $\mu_0 H \geq 4$ T slopes of the $M(H)$ data as shown by the solid symbols in Fig. 5. This observation confirms that the minor upturn in $\chi_{ab}(T)$ below ~ 10 K is indeed due to the presence of trace saturable impurities.

IV. DISCUSSION

Electrical transport measurements infer an insulating ground state in BaMn₂P₂ with activation energy $\Delta = 24(2)$ meV. Similar observations were earlier made on BaMn₂As₂ and BaMn₂Sb₂ (Table I). The $\rho_{ab}(T)$ of BaMn₂P₂ decreases exponentially with the increase of T until ~ 130 K and then remains nearly T independent up to ~ 200 K beyond which it decreases slightly with increase of T . This crossover indicates that similar to the As- and Sb-based analogs there is a possibility of the existence of more than one activation energies likely associated with different zones of the elec-

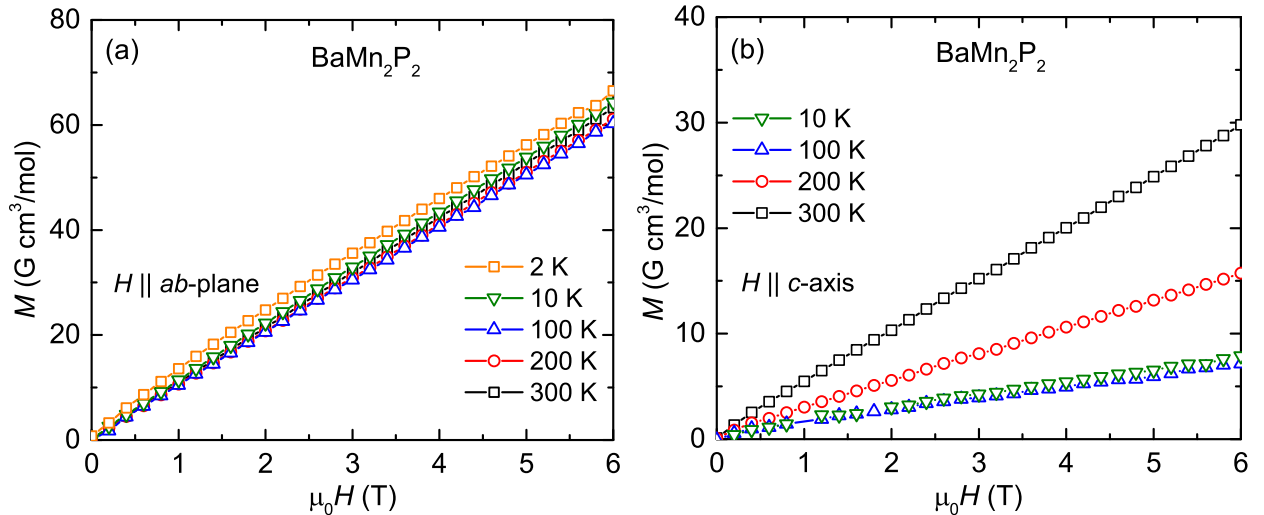


FIG. 7. Isothermal magnetization M vs applied magnetic field H of BaMn₂P₂ measured for two different crystal orientations; (a) $H \parallel ab$ plane and (b) $H \parallel c$ axis.

tronic bands dominating the electrical transport in different T regions. The $C_p(T)$ data lead to $\gamma = 0.9(9)$ mJ/mol K² corroborating the outcome of the electrical transport measurement and infer an insulating ground state in BaMn₂P₂. The Θ_D of BaMn₂P_n compounds decreases rapidly with the increase in atomic number of pnictide atom present in the lattice (Table I) inferring that the higher energy modes get enhanced with the inclusion of lighter elements in the lattice.

The insulating ground state of BaMn₂P₂ confirms that, similar to other BaMn₂P_n compounds, the underlying magnetism in this material is constituted by the localized spins residing on Mn ions. The anisotropic $\chi_{ab,c}(T)$ of BaMn₂P₂ clearly show the existence of a collinear AFM with the magnetic easy-axis parallel to the tetragonal c axis and $T_N = 795(15)$ K. The observed T_N in BaMn₂P₂ is highest among all the ThCr₂Si₂- and CaAl₂Si₂-type 122-pnictide compounds reported so far suggesting that the strength of magnetic exchange interactions is strongest in this material. The magnetic interactions within BaMn₂As₂ and BaMn₂Sb₂ have been successfully explained using J_1 - J_2 - J_c Heisenberg model of stacked-square lattice, where J_1 and J_2 are the NN and NNN intralayer exchange interactions, respectively, and J_c in the interlayer interaction acting along the c axis [35]. The similarity of the $\chi_{ab,c}(T)$ data of BaMn₂P₂ with those of the As-, Sb-, and Bi-analogs [25–27] suggest that magnetic interactions within this material can also be described using the same model. Interestingly, we have observed a monotonic decrease of T_N with the increase in a and c parameters. When moving from BaMn₂P₂ to BaMn₂Bi₂, about 12% increase in a and c leads to about $\sim 50\%$ decrease in T_N suggesting a strong dependence of J_1 , J_2 , and J_c on the intralayer as well as interlayer distances between the localized Mn spins. Further, the $\chi_{ab,c}(T)$ of BaMn₂P₂ show a monotonic increase for $T > T_N$. This behavior is similar to what was previously observed in As-, Sb-, and Bi-analogs [26,27,35] and suggests that dynamic short-range quasi-two-dimensional AFM correlations persist above T_N in this material as well.

It is interesting to compare the Mn-based insulating BaMn₂P_n compounds with the Co-based metallic ACo₂As₂ ($A = \text{Ca, Sr, Ba}$), which also crystallize in ThCr₂Si₂-type structure. ACo₂As₂ compounds exhibit properties that delicately depend upon the interlayer $d_{\text{As-As}}$, which regulates the oxidation state of Co ions in these materials by controlling the extent of the interlayer As-As bonds. As a result, it indirectly controls the magnetic ground state [9]. For example, BaCo₂As₂ with $d_{\text{As-As}} = 3.78$ Å shows a nonmagnetic ground state [36]. On the other hand, CaCo_{1.86}As₂ with $d_{\text{As-As}} = 2.73$ Å exhibits an A-type collinear AFM ordering below 52 K [37]. Interestingly, SrCo₂As₂ with $d_{\text{As-As}} = 3.33$ Å intermediate to those of its Ca and Ba analogs shows no evidence of long-range magnetic ordering, but exhibits stripe-type AFM [10] as well as FM [11] spin fluctuations, where the former is similar to the fluctuations observed in the FeAs-based superconductors. On the contrary, d_{Pn-Pn} does not show any significant variation within the BaMn₂P_n compounds and because of the localized nature of d bands it apparently does not have any direct effect on the oxidation state of the Mn ions as well as on the magnetic ground state of

these materials. ACo₂As₂ and BaMn₂P_n compounds together present a textbook type example of how the structural parameters and electronic band structure can indirectly govern the magnetism within crystalline systems. It is also noteworthy that the ground state crystal structure of AMn₂P_n compounds only depends upon the type of alkaline earth metal present in the lattice while the unit-cell dimensions are controlled by the pnictogen atoms constituting the lattice. This feature could further be used to investigate the structural crossover regions to understand structure-property relationship within this system and to explore instability driven phase transitions and ground states.

As BaMn₂P₂ has the highest T_N within this series, it would be very interesting to perform hole-doping studies on this material. A similar investigation in the related compound BaMn₂As₂ with $T_N = 618$ K has led to the discovery of a prototype itinerant half-metallic ferromagnetism with $T_c \approx 100$ K. It would be worth to investigate if the stronger exchange interactions resulting in large T_N in BaMn₂P₂ can assist in developing a half-metallic FM state with higher T_c . Such investigations would be important as the high- T_c half-metals are desirable candidates for spin-polarized device applications.

V. CONCLUSIONS

High-quality single crystals of BaMn₂P₂ were grown using Sn flux. The ab -plane electrical resistivity as well as the heat capacity measurements suggest a small band gap insulating ground state of the material. The anisotropic magnetic susceptibility $\chi_{ab,c}(T)$ measurements show that similar to BaMn₂P_n ($Pn = \text{As, Sb, Bi}$) compounds, BaMn₂P₂ has a collinear Néel-type AFM ground state with transition temperature $T_N = 795(15)$ K, which is highest among the 122-pnictide compounds investigated so far. The AFM transition temperatures of BaMn₂P_n compounds show a monotonic decrease with the increase of tetragonal a and c parameters, where about 12% increase in a and c leads to $\sim 50\%$ decrease in T_N . These observations suggest a strong dependence of the strength of the magnetic exchange interactions on the separation between the localized spins residing on the Mn ions. The $\chi_{ab,c}(T)$ of BaMn₂P₂ show a monotonic increase for $T > T_N$ suggesting the presence of sizable short-range dynamic quasi-two-dimensional AFM correlations above the T_N . Because of the high value of T_N of BaMn₂P₂, hole-doping investigations are highly sought for. Similar studies in related BaMn₂As₂ with $T_N = 618$ K have led to the discovery of prototypical itinerant half-metallic behavior of the doped holes with $T_c \approx 100$ K. Such investigations become more significant as half-metals with high- T_c are emerging as desirable candidates for spin-polarized transport-based applications.

ACKNOWLEDGMENTS

A.P. acknowledges the financial support from Faculty Research Committee and University Research Committee of the University of the Witwatersrand and National Research Foundation of South Africa. The work at Texas A&M University was supported by the National Science Foundation through Grant No. NSF-DMR-1807451.

- [1] Y. Kamihara, T. Watanabe, M. Hirano, and H. Hosono, Iron-Based layered superconductor La[O_{1-x}F_x]FeAs ($x = 0.05 - 0.12$) with $T_c = 26$ K, *J. Am. Chem. Soc.* **130**, 3296 (2008).
- [2] C. Wang, L. Li, S. Chi, Z. Zhu, Z. Ren, Y. Li, Y. Wang, X. Lin, Y. Luo, S. Jiang *et al.*, Thorium-doping-induced superconductivity up to 56 K in Gd_{1-x}Th_xFeAsO, *Europhys. Lett.* **83**, 67006 (2008).
- [3] J. Paglione and R. L. Greene, High-temperature superconductivity in iron-based materials, *Nat. Phys.* **6**, 645 (2010).
- [4] D. C. Johnston, The puzzle of high temperature superconductivity in layered iron pnictides and chalcogenides, *Adv. Phys.* **59**, 803 (2010).
- [5] G. R. Stewart, Superconductivity in iron compounds, *Rev. Mod. Phys.* **83**, 1589 (2011).
- [6] A. Pandey, B. G. Ueland, S. Yeninas, A. Kreyssig, A. Sapkota, Y. Zhao, J. S. Helton, J. W. Lynn, R. J. McQueeney, Y. Furukawa, A. I. Goldman, and D. C. Johnston, Coexistence of Half-Metallic Itinerant Ferromagnetism with Local-Moment Antiferromagnetism in Ba_{0.6}K_{0.4}Mn₂As₂, *Phys. Rev. Lett.* **111**, 047001 (2013).
- [7] B. G. Ueland, A. Pandey, Y. Lee, A. Sapkota, Y. Choi, D. Haskel, R. A. Rosenberg, J. C. Lang, B. N. Harmon, D. C. Johnston, A. Kreyssig, and A. I. Goldman, Itinerant Ferromagnetism in the As-4*p* Conduction Band of Ba_{0.6}K_{0.4}Mn₂As₂ Identified by X-Ray Magnetic Circular Dichroism, *Phys. Rev. Lett.* **114**, 217001 (2015).
- [8] A. Pandey and D. C. Johnston, Ba_{0.4}Rb_{0.6}Mn₂As₂: A prototype half-metallic ferromagnet, *Phys. Rev. B* **92**, 174401 (2015).
- [9] A. Pandey, D. G. Quirinale, W. Jayasekara, A. Sapkota, M. G. Kim, R. S. Dhaka, Y. Lee, T. W. Heitmann, P. W. Stephens, V. Ogloblichev, A. Kreyssig, R. J. McQueeney, A. I. Goldman, A. Kaminski, B. N. Harmon, Y. Furukawa, and D. C. Johnston, Crystallographic, electronic, thermal, and magnetic properties of single-crystal SrCo₂As₂, *Phys. Rev. B* **88**, 014526 (2013).
- [10] W. Jayasekara, Y. Lee, A. Pandey, G. S. Tucker, A. Sapkota, J. Lamsal, S. Calder, D. L. Abernathy, J. L. Niedziela, B. N. Harmon, A. Kreyssig, D. Vaknin, D. C. Johnston, A. I. Goldman, and R. J. McQueeney, Stripe Antiferromagnetic Spin Fluctuations in SrCo₂As₂, *Phys. Rev. Lett.* **111**, 157001 (2013).
- [11] Y. Li, Z. Yin, Z. Liu, W. Wang, Z. Xu, Y. Song, L. Tian, Y. Huang, D. Shen, D. L. Abernathy, J. L. Niedziela, R. A. Ewings, T. G. Perring, D. M. Pajerowski, M. Matsuda, P. Bourges, E. Mechtild, Y. Su, and P. Dai, Coexistence of Ferromagnetic and Stripe Antiferromagnetic Spin Fluctuations in SrCo₂As₂, *Phys. Rev. Lett.* **122**, 117204 (2019).
- [12] A. Sapkota, B. G. Ueland, V. K. Anand, N. S. Sangeetha, D. L. Abernathy, M. B. Stone, J. L. Niedziela, D. C. Johnston, A. Kreyssig, A. I. Goldman, and R. J. McQueeney, Effective One-Dimensional Coupling in the Highly Frustrated Square-Lattice Itinerant Magnet CaCo_{2-y}As₂, *Phys. Rev. Lett.* **119**, 147201 (2017).
- [13] V. K. Anand, H. Kim, M. A. Tanatar, R. Prozorov, and D. C. Johnston, Superconducting and normal-state properties of APd₂As₂ ($A = \text{Ca, Sr, Ba}$) single crystals, *Phys. Rev. B* **87**, 224510 (2013).
- [14] V. K. Anand, H. Kim, M. A. Tanatar, R. Prozorov, and D. C. Johnston, Superconductivity and physical properties of CaPd₂Ge₂ single crystals, *J. Phys.: Condens. Matter* **26**, 405702 (2014).
- [15] X. F. Wang, C. Roncaioli, C. Eckberg, H. Kim, J. Yong, Y. Nakajima, S. R. Saha, P. Y. Zavalij, and J. Paglione, Tunable electronic anisotropy in single-crystal ACr₃As₃ ($A = \text{K, Rb}$) quasi-one-dimensional superconductors, *Phys. Rev. B* **92**, 020508(R) (2015).
- [16] K. Zhao, Q.-G. Mu, B.-B. Ruan, T. Liu, B.-J. Pan, M.-H. Zhou, S. Zhang, G.-F. Chen, and Z.-A. Ren, Synthesis and superconductivity of a novel quasi-one-dimensional ternary molybdenum pnictide Cs₂Mo₃As₃, *APL Mater.* **8**, 031103 (2020).
- [17] A. Pandey, S. L. Samal, and D. C. Johnston, CsMn₄As₃: A Layered tetragonal transition-metal pnictide compound with an antiferromagnetic ground state, *Inorg. Chem.* **57**, 3206 (2018).
- [18] K.-K. Huynh, T. Ogasawara, K. Kitahara, Y. Tanabe, S. Y. Matsushita, T. Tahara, T. Kida, M. Hagiwara, D. Arçon, and K. Tanigaki, Negative and positive magnetoresistance in the itinerant antiferromagnet BaMn₂Pn₂ ($Pn = \text{P, As, Sb, and Bi}$), *Phys. Rev. B* **99**, 195111 (2019).
- [19] T. Ogasawara, K.-K. Huynh, T. Tahara, T. Kida, M. Hagiwara, D. Arçon, M. Kimata, S. Y. Matsushita, K. Nagata, and K. Tanigaki, Large negative magnetoresistance in the antiferromagnet BaMn₂Bi₂, *Phys. Rev. B* **103**, 125108 (2021).
- [20] T. Ogasawara, K.-K. Huynh, S. Y. Matsushita, M. Kimata, T. Tahara, T. Kida, M. Hagiwara, D. Arçon, and K. Tanigaki, Magnetic field induced Anderson localization in the orbital-selective antiferromagnet BaMn₂Bi₂, *Phys. Rev. B* **106**, L041114 (2022).
- [21] A. Mewis, AB₂X₂-Compounds with the CaAl₂Si₂ Structure, V [1] The crystal structure of CaMn₂P₂, CaMn₂As₂, SrMn₂P₂ and SrMn₂As₂, *Z. Naturforsch. B* **33**, 606 (1978).
- [22] G. Cordier and H. Schäfer, New intermetallic compounds in the anti-Ce₂O₂S-structure type, *Z. Naturforsch. B* **31**, 1459 (1976).
- [23] A. Pandey, R. S. Dhaka, J. Lamsal, Y. Lee, V. K. Anand, A. Kreyssig, T. W. Heitmann, R. J. McQueeney, A. I. Goldman, B. N. Harmon, A. Kaminski, and D. C. Johnston, Ba_{1-x}K_xMn₂As₂: An Antiferromagnetic Local-Moment Metal, *Phys. Rev. Lett.* **108**, 087005 (2012).
- [24] A. T. Satya, A. Mani, A. Arulraj, N. V. C. Shekar, K. Vinod, C. S. Sundar, and A. Bharathi, Pressure-induced metallization of BaMn₂As₂, *Phys. Rev. B* **84**, 180515(R) (2011).
- [25] Y. Singh, A. Ellern, and D. C. Johnston, Magnetic, transport, and thermal properties of single crystals of the layered arsenide BaMn₂As₂, *Phys. Rev. B* **79**, 094519 (2009).
- [26] N. S. Sangeetha, V. Smetana, A.-V. Mudring, and D. C. Johnston, Antiferromagnetism in semiconducting SrMn₂Sb₂ and BaMn₂Sb₂ single crystals, *Phys. Rev. B* **97**, 014402 (2018).
- [27] B. Saparov and A. S. Sefat, Crystals, magnetic and electronic properties of a new ThCr₂Si₂-type BaMn₂Bi₂ and K-doped compositions, *J. Solid State Chem.* **204**, 32 (2013).
- [28] S. Calder, B. Saparov, H. B. Cao, J. L. Niedziela, M. D. Lumsden, A. S. Sefat, and A. D. Christianson, Magnetic structure and spin excitations in BaMn₂Bi₂, *Phys. Rev. B* **89**, 064417 (2014).
- [29] S. L. Brock, J. E. Greedan, and S. M. Kauzlarich, A test of the application of extended Hückel calculations to the ThCr₂Si₂ and CaAl₂Si₂ structure types: The case of SrMn₂P₂ and BaMn₂P₂, *J. Solid State Chem.* **109**, 416 (1994).
- [30] S. L. Brock, J. E. Greedan, and S. M. Kauzlarich, Resistivity and magnetism of AMn₂P₂ ($A = \text{Sr, Ba}$): The effect of structure type on physical properties, *J. Solid State Chem.* **113**, 303 (1994).

- [31] P. C. Canfield, New materials physics, [Rep. Prog. Phys.](#) **83**, 016501 (2020).
- [32] J. Rodríguez-Carvajal, Recent advances in magnetic structure determination by neutron powder diffraction, [Phys. B: Condens. Matter](#) **192**, 55 (1993); see also www.ill.eu/sites/fullprof/.
- [33] R. J. Goetsch, V. K. Anand, A. Pandey, and D. C. Johnston, Structural, thermal, magnetic, and electronic transport properties of the $\text{LaNi}_2(\text{Ge}_{1-x}\text{Px})_2$ system, [Phys. Rev. B](#) **85**, 054517 (2012).
- [34] E. S. R. Gopal, *Specific Heats at Low Temperatures* (Plenum, New York, 1966).
- [35] D. C. Johnston, R. J. McQueeney, B. Lake, A. Honecker, M. E. Zhitomirsky, R. Nath, Y. Furukawa, V. P. Antropov, and Yogesh Singh, Magnetic exchange interactions in BaMn_2As_2 : A case study of the J_1 - J_2 - J_c Heisenberg model, [Phys. Rev. B](#) **84**, 094445 (2011).
- [36] V. K. Anand, D. G. Quirinale, Y. Lee, B. N. Harmon, Y. Furukawa, V. V. Ogloblichev, A. Huq, D. L. Abernathy, P. W. Stephens, R. J. McQueeney, A. Kreyssig, A. I. Goldman, and D. C. Johnston, Crystallography and physical properties of BaCo_2As_2 , $\text{Ba}_{0.94}\text{K}_{0.06}\text{Co}_2\text{As}_2$, and $\text{Ba}_{0.78}\text{K}_{0.22}\text{Co}_2\text{As}_2$, [Phys. Rev. B](#) **90**, 064517 (2014).
- [37] V. K. Anand, R. S. Dhaka, Y. Lee, B. N. Harmon, A. Kaminski, and D. C. Johnston, Physical properties of metallic antiferromagnetic $\text{CaCo}_{1.86}\text{As}_2$ single crystals, [Phys. Rev. B](#) **89**, 214409 (2014).